

## Review article:

# PARTICLES FROM PREFORMED POLYMERS AS CARRIERS FOR DRUG DELIVERY

K. Miladi<sup>a,b</sup>, D. Ibraheem<sup>a</sup>, M. Iqbal<sup>a</sup>, S. Sfar<sup>b</sup>, H. Fessi<sup>a</sup>, A. Elaissari<sup>a\*</sup>

<sup>a</sup> University of Lyon, F- 69622, Lyon, France; Lyon 1 University, Villeurbanne, CNRS, UMR 5007, Laboratoire d'Automatique et de Génie des Procédés, LAGEP-CPE-308G, 43 bd. du 11 Nov.1918, F-69622, Villeurbanne, France

<sup>b</sup> University of Monastir, Laboratoire de pharmacie galénique, Rue Avicenne, 5000 Monastir, Tunisia

\* Corresponding author: Phone: +33-472431841, Fax: +33-472431682  
E-mail: elaissari@lagep.univ-lyon1.fr

## ABSTRACT

Biodegradable and biocompatible polymers are widely used for the encapsulation of drug molecules. Various particulate carriers with different sizes and characteristics have been prepared by miscellaneous techniques. In this review, we reported the commonly used preformed polymer based techniques for the preparation of micro and nano-structured materials intended for drug encapsulation. A description of polymer-solvent interaction was provided. The most widely used polymers were reported and described and their related research studies were mentioned. Moreover, principles of each technique and its crucial operating conditions were described and discussed. Recent applications of all the reported techniques in drug delivery were also reviewed.

**Keywords:** Drug delivery, particles, polymer, encapsulation, carriers, operating conditions

## INTRODUCTION

Particulate carriers have gained tremendous interest during the last decades which permitted to deliver many hydrophilic and hydrophobic molecules. Obtained particles present small size which facilitates their absorption. These drug delivery systems protect active pharmaceutical ingredients from degradation, enhance biopharmaceutical properties and could provide passive or active targeting or sustained delivery. Biomedical applications of the developed carriers are continuously growing (Ahmad, 2013; Soares, 2013; Miladi et al., 2013). Although, they present different physico-chemical properties, the used polymers are

mainly biocompatible and biodegradable. A multitude of techniques are used to obtain these particles. These methods differ by their principles and the nature of drug molecules that could be encapsulated. Some successfully marketed products led to an enlargement of the applications and the interest given by researchers to these drug delivery systems. Choice of the technique and operating conditions is crucial to obtain formulations bearing good properties for *in vitro* and *in vivo* applications. In this review, we will focus on polymeric particles and give a scope about the most used polymers. We will also describe the common preformed polymer based techniques used

for the encapsulation of drug molecules. We will also review the major applications of the developed particles during the last years and their main properties.

## 1. POLYMER-SOLVENT INTERACTIONS

Many techniques that rely on preformed polymers have been used for the preparation of particulate carriers. Although these methods are quite different, they generally share a unique principle which is polymer precipitation. Precipitation of the polymer occurs either when a non solvent is added or after subsequent decrease of its solubility in a solvent. Many parameters could influence polymer solubility such as, solvent nature, pH, salinity and temperature of the dispersion medium. Solubility of polyelectrolytes in water, for example, is highly pH and salinity dependent (Gennes, 1979), while that of poly(alkyl acrylamide) and poly(alkyl methacrylamide), is mainly temperature dependent (Elaissari, 2002). In fact, nanoprecipitation and emulsion based techniques are based on the addition of a non solvent to the polymer which causes its precipitation. However, ionic gelation technique, for instance, in which generally a polyelectrolyte is used as polymer, is based on the addition of a salt or an oppositely charged polymer. This results in a change in the salinity of the medium and the appearance of electrostatic interactions and thus, leads to polymer precipitation. The thermodynamic behavior of the polymer in a given solution is highly dependent on the Flory  $\chi$ -parameter. This parameter is defined as the free energy change per solvent molecule (in  $k_B T$  units) when a solvent-solvent contact is shifted to a solvent-polymer contact. It is expressed by the following mathematical equations:

$$\chi = \frac{\Delta G}{k_B T} = \frac{\Delta H - T\Delta S}{k_B T} = \frac{1}{2} - A\left(1 - \frac{\theta}{T}\right)$$

Equation (1)

where  $k_B$  and  $T$  are Boltzmann constant and temperature, respectively;  $A$  and  $\theta$  parameters are defined as follows:

$$A = \frac{2\Delta S + k_B}{2k_B}$$

Equation (2)

$$\theta = \frac{2\Delta H}{2\Delta S + k_B}$$

Equation (3)

It can be seen that the  $A$  parameter is directly related to entropy changes, whereas  $\theta$  temperature is a function of both entropic and enthalpic variations. When  $\theta$  temperature =  $T$ , the corresponding Flory  $\chi$ -parameter =  $1/2$ , at which the second Virial coefficient is equal zero (Elias, 2003). The latter can be easily determined from light scattering measurements of a diluted polymer solution. At  $\theta$  temperature conditions, the binary interactions among constituents will be negligible and only the excluded volume effects will be predominant. Consequently, the solvent will be a good solvent for the polymer when  $\chi < 1/2$  and a poor one when  $\chi > 1/2$  (Minost et al., 2012).

## 2. COMMONLY USED POLYMERS FOR ENCAPSULATION

Several polymers have been used for drug encapsulation but only biodegradable and biocompatible ones are suitable for biomedical applications. The biodegradability of a polymer is acquired by the presence of a labile function such as ester, orthoester, anhydride, carbonate, amide, urea or urethane in their backbone. These polymers could be of natural (polysaccharides and protein based polymers) or synthetic (polyesters) nature (Pillai and Panchagnula, 2001). The most commonly used polymers for drug encapsulation are polyesters (lactide and glycolide copolymers, poly- $\epsilon$ -caprolactone), acrylic polymers (polymethacrylates) and polyamides (gelatin and albumin). The selection of the right polymer is a crucial step to obtain particles that are suitable for a well-defined application. In fact, polymers' structures are highly differ-

ent and their surface and bulk properties are highly relevant for the obtaining of the desirable biological application. Copolymers could be also used to monitor the hydrophobicity of the materials. Some polymers are poly(ethyleneglycol) (PEG) copolymerized in order to decrease nanoparticle recognition by the reticular endothelial sys-

tem. Table 1 contains examples of the most used biocompatible and biodegradable polymers in encapsulation. Some polymers, especially those having mucoadhesive properties, could also be used for coating the nanocarriers (Mazzaferro et al., 2012; Zandanel and Vauthier, 2012).

**Table 1:** Commonly used polymers

Materials	References
<b>Polymers</b>	
<i>Natural polymers</i>	
Chitosan	Elmizadeh et al., 2013; Fàbregas et al., 2013; Khalil et al., 2012; Konecni et al., 2012; Du et al., 2009; Bernkop-Schnürch et al., 2006; Gan et al., 2005; Asada et al., 2004
Dextran	Liang et al., 2013; Dai et al., 2012; Sajadi Tabassi et al., 2008; Koten et al., 2003
Dextran derivatives	Kanthamneni et al., 2012; Kauffman et al., 2012; Aumelas et al., 2007; Miyazaki et al., 2006
Cyclodextrins	Çirpanli et al., 2009; Memişoğlu et al., 2003; Pariot et al., 2002; Lemos-Senna et al., 1998
Gelatin	Nahar et al., 2008; Balthasar et al., 2005; Vandervoort and Ludwig, 2004; Bruschi et al., 2003
<i>Synthetic polymers</i>	
<i>Biodegradable polyesters</i>	
PLGA	Gyulai et al., 2013; Beck-Broichsitter et al., 2012; Morales-Cruz et al., 2012; Beck-Broichsitter et al., 2011; Nehilla et al., 2008; Song et al., 2008; Budhian et al., 2007; Bozkir and Saka, 2005; Fonseca et al., 2002; Yang et al., 1999; Govender et al., 1999
PLA	Bazylińska et al., 2013; Fredriksen and Grip 2012; Kadam et al., 2012; Kumari et al., 2011; Ataman-Önal et al., 2006; Lamalle-Bernard et al., 2006; Hyvönen et al., 2005; Katare et al., 2005; Chorny et al., 2002; Leo et al., 2000
PCL	Behera and Swain, 2012; Guerreiro et al., 2012; Hernán Pérez de la Ossa et al., 2012; Khayata et al., 2012; Arias et al., 2010; Wang et al., 2008; Limayem Blouza et al., 2006; Tewa-Tagne et al., 2006; Yang et al., 2006; Le Ray et al., 2003; Chawla and Amiji 2002; Raval et al., 2011; Hombreiro Pérez et al., 2000; Benoit et al., 1999; Masson et al., 1997
Poly(lactide-co-glycolide-co-caprolactone)	Zhang et al., 2006
<i>Acrylic polymers</i>	
Eudragit	Hao et al., 2013; Das et al., 2010; Eidi et al., 2010; Trapani et al., 2007; Galindo-Rodríguez et al., 2005; Haznedar and Dortunç 2004; Pignatello et al., 2002
<i>Others</i>	
Polyvinylbenzoate	Labruère et al., 2010
<i>Pegylated polymers</i>	
Chitosan-PEG	Seo et al., 2009
MPEG-PCL	Falamarzian and Lavasanifar, 2010; Xin et al., 2010
PCL-PEG-PCL	Suksiriworapong et al., 2012; Huang et al., 2010; Gou et al., 2009
Poly(caprolactone)-poly(ethylene oxide)-poly(lactide)	Hu et al., 2003
PLA-PEG	Sacchetin et al., 2013; Essa et al., 2010; Ishihara et al., 2010; Vila et al., 2005; Vila et al., 2004; Govender et al., 2000; Huang et al., 1997
PLA-PEG-PLA	Chen et al., 2011; Ruan and Feng 2003
MPEG-PLA	Zheng et al., 2010; Dong and Feng, 2007; Dong and Feng, 2004

## 2.1 Natural polymers

### 2.1.1 Chitosan

Chitosan is obtained by deacetylation of chitin, which is the structural element in the exoskeleton of crustaceans (crabs, shrimp, etc.) and cell walls of fungi. It is a cationic and biodegradable polysaccharide consisting of repeating D-glucosamine and N-acetyl-D-glucosamine units, linked via (1-4) glycosidic bonds. Chitosan is non toxic and can be digested in the physiological environment, either by lysozymes or by chitinases, which are present in the human intestine and in the blood. These properties led to increased interest for this polymer in pharmaceutical research and industry as a carrier for drug delivery (Mao et al., 2010). In addition, chitosan has mucoadhesive properties owing to its positive charge that allows interaction with the negatively-charged mucosal surface. Consequently, the use of chitosan as a matrix (Patil and Sawant, 2011) or as a coating material (Mazzarino et al., 2012) in drug encapsulation had become a promising strategy to prolong the residence time, to increase the absorption of active molecules through the mucosa (Mao et al., 2010; Alpar et al., 2005) and also for targeted delivery (Park et al., 2010).

### 2.1.2 Dextran and its derivatives

Dextran polymers are produced by bacteria from sucrose. Chemical synthesis is also possible. These glucose polymers consist predominantly of linear  $\alpha$ -1,6-glycosidic linkage with some degree of branching via 1,3-linkage. Dextran-based microspheres have got much attention because of their low toxicity, good biocompatibility and biodegradability, which are of interest for application in biomedical and pharmaceutical fields (Mehvar, 2000). Many dextran polymers such as Sephadex® (cross-linked dextran microspheres) as well as Spherex® (cross-linked starch microspheres) were used as carriers for drug delivery. Other derivatives of dextran and

starch including diethyl aminoethyl dextran and polyacryl starch have also been used for mucosal drug delivery. Illum et al. (2001) proposed some mechanisms to explain absorption enhancement effects of cross-linked starch and dextran microspheres intended to nasal delivery which are: (1) Deposition of the microspheres in the less or non ciliated anterior part of the nasal cavity and slower nasal clearance; (2) Retention of the formulation in the nasal cavity for an extended time period because of the bioadhesive properties of the microspheres and (3) The local high drug concentration provided by the gelled system in close contact with the epithelial absorptive surface (Illum et al., 2001).

### 2.1.3 Cyclodextrins

Cyclodextrins (CDs) are cyclic oligosaccharides that contain at least six D-(+) glucopyranose units which are attached by  $\alpha$ -(1,4) glycosidic bonds. They have been widely used for the formulation of drugs with bioavailability concerns resulting from poor solubility, poor stability and severe side effects. There are 3 natural CDs which are  $\alpha$ -,  $\beta$ -, and  $\gamma$ -CDs (with 6, 7, or 8 glucose units respectively) (Challa et al., 2005). In addition, amphiphilic cyclodextrins are synthetic derivatives of natural cyclodextrins. Such derivatives are able to self-organize in water to form micelles and nano-aggregates, which is interesting for pharmaceutical applications, mainly, encapsulation (Gèze et al., 2002). In fact, amphiphilic cyclodextrins have recently been used to prepare nanoparticles and nanocapsules without surfactants and have shown high drug-loading capacity with favorable release properties (Lemos-Senna et al., 1998; Çirpanli et al., 2009; Duchêne, 1999). They have also been used for targeting and for increasing drug loading (Duchêne et al., 1999).

### 2.1.4 Gelatin

Gelatin is a natural polymer that is derived from collagen. It is commonly used for pharmaceutical and medical applications because of its biodegradability and biocompatibility in physiological environments. Gelatin is attractive for use in controlled release due to its nontoxic, bioactive properties and inexpensive price. It is also a polyampholyte having both cationic and anionic groups along with hydrophilic groups. Mechanical properties, swelling behavior and thermal properties of gelatin depend significantly on its crosslinking degree (Young et al., 2005).

## 2.2 Biodegradable polyesters

Polyester-based polymers are among of the most widely investigated materials for drug delivery. Poly(lactic acid) (PLA), poly(glycolic acid) (PGA) and their copolymers poly(lactic acid-co-glycolic acid) (PLGA) along with poly- $\epsilon$ -caprolactone are some of the well-defined biomaterials with regard to design and performance for drug-delivery applications.

### 2.2.1 PLGA

PLGA, a copolymer of lactic acid and glycolic acid, has generated tremendous interest due to its excellent biocompatibility, biodegradability, and mechanical strength. PLGA is approved by the US FDA and European Medicine Agency (EMA) in various drug delivery systems in humans. In order to improve the formulation of controlled drug delivery systems, an understanding of the physical, chemical, and biological properties of polymers is helpful. In fact, the polymer is commercially available with different molecular weights and copolymer compositions. The degradation time can vary from several months to several years, depending on the molecular weight and copolymer ratio (Danhier et al., 2012). For example, lactic acid is more hydrophobic than glycolic acid and, therefore, lactide-rich PLGA copoly-

mers are less hydrophilic, absorb less water, and subsequently, degrade more slowly (Dinarvand et al., 2011). PLGA particles are widely used to encapsulate active molecules with a broad spectrum of pharmaceutical applications (Danhier et al., 2012; Menei et al., 2005; Singh et al., 2004).

### 2.2.2 PLA

PLA is a biocompatible and biodegradable synthetic polyester which undergoes scission in the body to monomeric units of lactic acid. The latter is a natural intermediate in carbohydrate metabolism. PLA possess good mechanical properties and it is largely used for the preparation of particles (Gupta and Kumar, 2007).

### 2.2.3 PCL

It was in 1930s that the ring-opening polymerization of PCL was studied. The biodegradable property of this synthetic polymer was first identified in 1973. PCL is suitable for controlled drug delivery due to its high permeability to many drugs and non-toxicity (Sinha et al., 2004). Molecular weight dependent surface hydrophobicity and crystallinity of PCL are the causes for its slower biodegradation in two distinct phases such as random non-enzymatic cleavage and enzymatic fragmentation. Lipophilic drugs are generally distributed uniformly in the matrix while hydrophilic drugs tend to move towards the interface and remain on the surface of PCL formulation in adsorbed state. Diffusion was described as the only possible mechanism by which the lipophilic drugs release from PCL particles as they were shown to be intact for a much longer duration *in vivo*. However, two phenomena could be implicated in hydrophilic drugs' release. Highly lipophilic drugs that resist complete diffusion are released upon surface erosion by enzymatic action while hydrophilic drugs that accumulate at the interface during the formulation processes are released by desorption at the initial period of release study

or dosage intake. This results in a biphasic drug release pattern for PCL particles with much higher burst release for hydrophilic drugs than lipophilic ones (Dash and Konkimalla, 2012).

### 2.3 Pegylated polymers

Many of the above cited polymers could be conjugated to PEG chains, which allows the enhancement of their hydrophilicity and permits the obtaining of a stealth surface that could protect the prepared carriers from degradation by the cells belonging to the reticuloendothelial system. Conjugation to PEG confers also bioadhesive properties for the carriers (Yoncheva et al. 2005).

## 3. Used methods for the encapsulation of active molecules

### 3.1 Nanoprecipitation

The nanoprecipitation technique was first developed by Fessi et al. in 1986 (Devissaguet et al., 1991). The technique allows the obtaining of either nanospheres or nanocapsules. The organic phase could be added to the aqueous phase under magnetic stirring. This one-step process allows the instantaneous and reproducible formation of monodisperse nanoparticles. Nanoprecipitation is simple, is by far the fastest, most reproducible, and industrially feasible preparation procedure of nanospheres (Vauthier and Bouchemal, 2009). Practically, two miscible phases are required: an or-

ganic solvent in which the polymer is dissolved and an aqueous phase (non-solvent of the polymer). The most common used organic solvents are ethanol and acetone. Such solvents are miscible in water and easy to remove by evaporation. Some oils could be added to these solvents to allow the dissolving of the active (Rosset et al., 2012). As Figure 1 shows, the method is based on the addition of one phase to the other under moderate magnetic stirring which causes the interfacial deposition of a polymer after displacement of the organic solvent from the organic solution. This leads to the formation of a suspension of nanoparticles. The organic phase could be a mixture of solvents such as, mixture of acetone with water or ethanol etc. Similarly, the aqueous phase could consist of a mixture of non-solvents and could contain surfactants. Commonly used polymers are biodegradable polyesters, especially PCL, PLA and PLGA (Rao and Geckeler, 2011). Particle formation process includes three basic steps which are, particle nucleation, molecular growth and aggregation. The rate of every step has a crucial impact on the particle size distribution. Supersaturation is the driving force that manages all of these steps, namely, particles nucleation rate. Supersaturation, itself, is influenced by fluid dynamics and mixing. In fact, low stirring rate results in low nucleation rates while higher mixing rates give high nucleation rates (Lince et al., 2008).

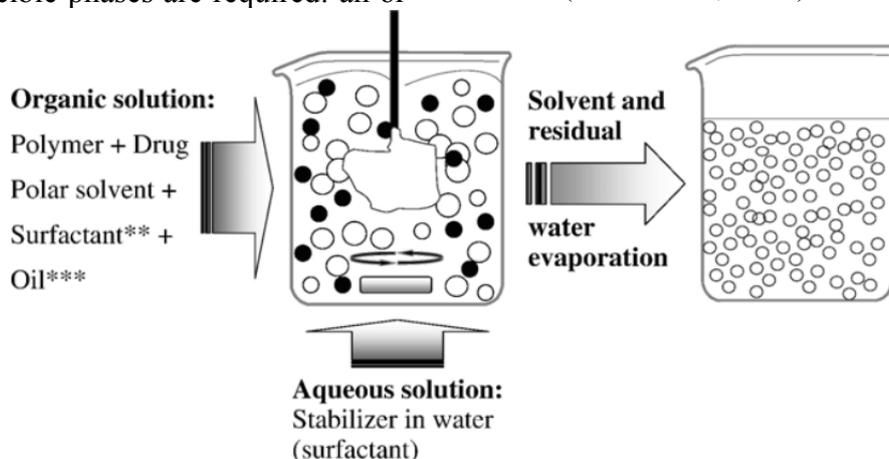


Figure 1: The nanoprecipitation technique (Pinto Reis et al., 2006)

Operational parameters that should be controlled include the organic phase to non organic phase ratio, the concentration of the polymer and the stabilizer and the amount of the drug. Every one of these parameters may exert an impact on the characteristics of the obtained nanoparticles (size, uniformity and charge). In fact, an increase of the polymer amount generally increases particles' size (Chorny et al., 2002; Simşek et al., 2013; Dong and Feng, 2004; Asadi et al., 2011). The same effect was obtained after increasing the polymer molecular weight (Limayem Blouza et al., 2006; Holgado et al., 2012). These findings were explained by an increase of the viscosity of the organic phase which rendered solvent diffusion more difficult and thus, led to larger nanoparticles' size. The effect of increasing organic phase volume seems conflicting: some studies showed that it causes a decrease of the particles size (Dong and Feng, 2004) while others showed the opposite phenomenon (Asadi et al., 2011). Increasing the water phase amount leads to a decrease of the particles size as a result of the increased diffusion of the water-miscible solvent in the aqueous phase and thus, the more rapid precipitation of the polymer and formation of nanoparticles (Budhian et al., 2007). An increase of the surfactant amount generally causes a decrease of the particles size and reduces size distribution (Contado et al., 2013; Siqueira-Moura et al., 2013). Some studies did not, however, found significant change following surfactant amount increase (Dong and Feng, 2004). The nature of the surfactant may also influence the particles' size (Limayem Blouza et al., 2006). Increasing mixing rate decreases the particles size as it causes faster diffusion rate (Asadi et al., 2011). Theoretical drug loading may also influence particles size and drug loading (Govender et al., 1999). Nanoprecipitation is generally designed for the encapsulation of hydrophobic drug molecules (Seju et al., 2011; Katara and Majumdar, 2013; Seremeta et al., 2013). Such actives may be

dissolved within the organic phase. Bilalti et al. (2005) described a nanoprecipitation technique intended to the encapsulation of hydrophilic molecules but the size of the obtained particles was not sufficiently uniform (Bilati et al., 2005). To further improve the reproducibility of the nanoprecipitation technique and make it more convenient for industrial applications, membrane contactor and microfluidic technology were successfully used (Khayata et al., 2012; Xie and Smith, 2010). These techniques allow better size control within different batches of particles. Table 2 contains some examples of the applications of the nanoprecipitation technique in drug delivery during the last years. It can be concluded that polyesters are among the most used polymers for the preparation of the nanoparticles by this technique.

### 3.2 Emulsion diffusion (ESD)


ESD was first developed by Quintanar-Guerrero and Fessi (Quintanar-Guerrero et al., 1996) to prepare PLA based nanospheres. Three liquid phases are needed in this technique: an organic phase, an aqueous phase and a dilution phase. The organic phase generally contains the polymer and the hydrophobic drug. The aqueous phase is a solution of a stabilizing agent while the dilution phase usually consists of a large volume of water. Mutual saturation of the aqueous and organic phase allows further obtaining of a thermodynamically equilibrated emulsion upon high speed homogenization. Subsequent addition of an excess of water enables the diffusion of the organic solvent from the dispersed phase resulting in precipitation of the polymer and the formation of the particles (Figure 2). Commonly used polymers in this method include PCL, PLA and Eudragit® (Mora-Huertas et al., 2010). Table 3 shows that the technique is mainly used for the encapsulation of hydrophobic molecules. However, hydrophilic molecules may also be encapsulated by a modified solvent diffusion method using an aqueous inner phase (Ma

et al., 2001). Operating conditions affecting the size of the obtained particles include external/internal phase ratio, emulsification stirring rate, volume and temperature of water for dilution, polymer amount and concentration of the stabilizer (Quintanar-Guerrero et al., 1996; Mora-Huertas et al., 2010). Influence of high shear homogenization and sonication on the particles size was assessed and it was found that sonication was more efficient for particle size reduction. The nature of the surfactant influenced also the particles size. In fact, when Pluronic F68 (PF68), didodecyl dimethylammonium bromide (DMAB) and polyvinylalcohol (PVA) were compared, DMAB gave the smallest particles but with the lowest encapsulation efficiency (Jain et al., 2011). Particles size was also described to increase with an increase of initial drug amount (Youm et al., 2012), polymer

amount (Youm et al., 2012; Esmaeili et al., 2011) and the oil phase volume (Esmaeili et al., 2011; Poletto et al., 2008). An increase of the surfactant amount resulted in a decrease of the size but it seems that above some level further significant size reduction is no longer possible (Jain et al., 2011; Surassmo et al., 2010). An increase of the homogenization rate led to a decrease of the particles' size (Jain et al., 2011; Kwon et al., 2001; Galindo-Rodríguez et al., 2005). Likely, the same effect was obtained following an increase of the temperature and the volume of added water (Kwon et al., 2001; Song et al., 2006). The nature of the organic solvent also influenced particle size (Song et al., 2006). Table 3 shows some of the recent applications of the ESD technique.

**Table 2:** Applications of the nanoprecipitation technique

Encapsulated molecule	Polymer	Size (nm)	Zeta potential (mV)	Reference
Doxorubicin	Gelatin-co-PLA-DPPE	131.5-161.1	-	Han et al., 2013
Aceclofenac	Eudragit RL 100	75.5-184.4	22.5 - 32.6	Katara and Majumdar, 2013
Doxorubicin	Dextran-b-polycaprolactone	95-123.3	-	Li et al., 2013
Chloroaluminum phthalocyanine	PLGA	220.3-326.3	-17.7-(-40.9)	Siqueira-Moura et al., 2013
Efavirenz	PCL and Eudragit® RS 100	89.5 - 173.9	-17.9-53.8	Seremeta et al., 2013
Paclitaxel	PLGA	50 - 150	-15 - (-20)	Wang et al., 2013
Retinoic acid	PLA	153.6-229.8	-27.4-(-20.9)	Almouazen et al., 2012
Brimonidine Tartrate	Eudragit® RL 100	123.5 - 140.2	13.1- 20.8	Khan et al., 2012
Vitamin E	PCL	123-320	-24.5-(-1.46)	Khayata et al., 2012
Paclitaxel	Hydrophobized pullulan	127.6-253		Lee et al., 2012
Curcumin	PCL, chitosan	104-125	(-0.099)-79.8	Mazzarino et al., 2012
Diclofenac	PCL	152	-50	Mora-Huertas et al., 2012
Amphotericin B	PLGA	86-153	-31.4-(-9.1)	Van de Ven et al., 2012
Epirubicin	Poly(butyl cyanoacrylate)	217-235	-4.5-(-0.1)	Yordanov 2012
Camptothecin	Beta-cyclodextrin	281	-13	Cirpanlı et al., 2011
	PLGA	187	-0.06	
	PCL	274	-19	
Naringenin	Eudragit® E	90	-	Krishnakumar et al., 2011
Olanzapine	PLGA	91.2	-23.7	Seju et al., 2011

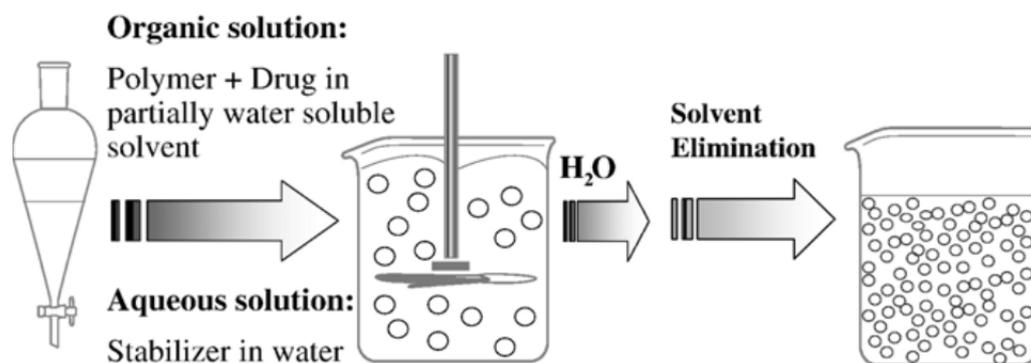

**Figure 2:** Emulsion diffusion technique (Pinto Reis et al., 2006)

**Table 3:** Applications of the emulsion diffusion method

Encapsulated molecule	Polymer	Size ( $\mu\text{m}$ )	Zeta potential (mV)	Reference
Articaine	PCL	-	-	Campos et al., 2013
Omeprazole	Eudragit L 100-55	0.256.3- 0.337	8.92 - 16.53	Hao et al., 2013
Curcumin	Polyurethane and polyurea	0.216- 4.901	-	Souguir et al., 2013
Matricaria recutita L. extract	PEG-PBA-PEG	0.186- 0.446	-	Esmaeili et al., 2011
Bovine serum albumin	Chitosan	81-98	-	Karnchanajindanun et al., 2011
Alendronate	PLGA	0.145	-4.7	Cohen-Sela et al., 2009
An oligonucleotide	PLA	0.390	-	Delie et al., 2001


### 3.3 Simple Emulsion evaporation (SEE)

The SEE technique is widely used in the field of particulate carriers' development. This method was first developed by (Vanderhoff et al., 1979). It consists on the formation of a simple emulsion followed by the evaporation of the organic solvent. Subsequent precipitation of the polymer allows the obtaining of the particles (Figure 3). Practically, for oil in water emulsion method, the polymer is dissolved in a volatile and non miscible organic solvent such as chloroform, ethylacetate or dichloromethane. This organic phase, in which the drug and the polymer are dissolved, is then dispersed by high speed homogenization or by sonication in an aqueous phase containing a surfactant. Once an oil-in-water (o/w)

emulsion is obtained, the evaporation of the organic solvent permits the precipitation of the polymer and thus, the formation of the particles. As it can be seen in Table 4, SEE is generally used for the encapsulation of hydrophobic drugs (O'Donnell and McGinity, 1997). The evaporation of the organic solvent is obtained by moderately stirring the emulsion at room temperature or under high temperature and low pressure conditions. The obtained particles can be then harvested by ultracentrifugation or filtration, then washed and lyophilized. Membrane technology was also used to prepare particles by the simple emulsion technique (Doan et al., 2011). Another alternative of the technique is the use of water in oil emulsion method that is suitable for the encapsulation of hydrophilic active molecules. Particulate carriers are obtained after evap-

oration of the water phase which causes the precipitation of the hydrophilic polymer (Banerjee et al., 2012). Parameters that have to be managed include organic phase to water phase ratio, nature of the surfactant and its concentration, stirring rate, polymer amount and evaporation rate. Decreasing the organic solvent volume resulted generally in a decrease of particle size (Budhian et al., 2007). Particle size could also be decreased by increasing surfactant amount (Valot et al., 2009; Manchanda et al., 2010; Khaled et al., 2010; Su et al., 2009), increa-

sing stirring rate (Su et al., 2009; Lee et al., 2012; Avachat et al., 2011; Yadav and Sawant, 2010) or increasing aqueous phase volume (Adibkia et al., 2011). However, an increase of polymer amount generally increases particles' size (Doan et al., 2011; D'Aurizio et al., 2011; Adibkia et al., 2011; Agnihotri and Vavia, 2009). Table 4 shows the applications of the SEE technique in drug delivery. Polyesters were widely used for the encapsulation of hydrophobic drugs.

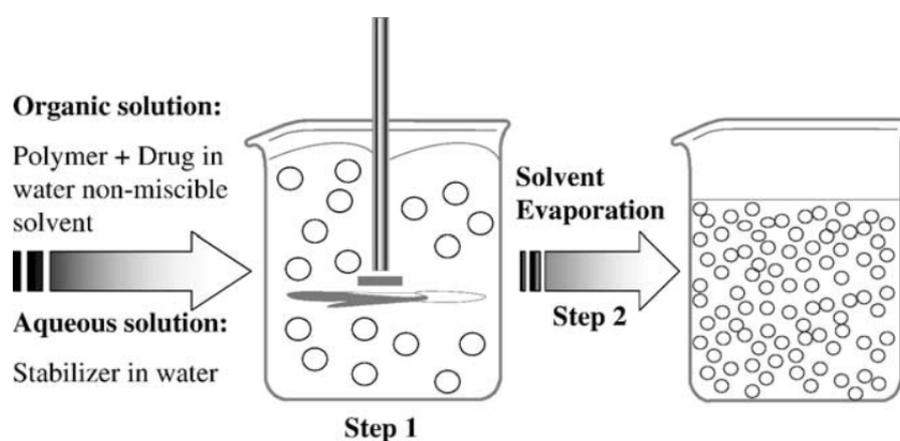

**Figure 3:** Simple emulsion solvent evaporation (Pinto Reis et al., 2006)

**Table 4:** Applications of simple emulsion solvent evaporation technique

Encapsulated molecule	Polymer	Size ( $\mu\text{m}$ )	Zeta potential (mV)	Reference
Curcumin	PLGA and PLGA-PEG	0.161-0.152	-	Khalil et al., 2013
Efavirenz	PCL and Eudragit® RS 100	0.083-0.219	53	Seremeta et al., 2013
Human amylin	PCL	0.202	-	Guerreiro et al., 2012
Azithromycin	PLGA	14.11-15.29	-	Li et al., 2012
Teniposide	PLGA	0.113-0.135	-36.6-(-23.1)	Mo et al., 2012
Camptothecin	PCL-PEG-PCL	4.2-5.4	-	Dai et al., 2011
Naproxen	PLGA	352-824	-	Javadzadeh et al., 2010
Doxorubicin	PLGA	0.137-0.164	-12.3-(-9.9)	Manchanda et al., 2010
Dexamethasone	PLGA	5.18-7	-	Rawat and Burgess, 2010
Ibuprofen	Eudragit RSPO	14-51.1	-	Valot et al., 2009

### 3.4 Double emulsion evaporation (DEE)

Double emulsion technique is suitable for the encapsulation of hydrophilic molecules (see Table 5 and Figure 4). Generally, the method consists on the dispersion of an aqueous phase in a non miscible organic solvent to form the first emulsion (W1/O). This dispersion is performed under high shear homogenization or low power sonication for a short time. This step is followed by the dispersion of the obtained emulsion in a second aqueous phase containing a hydrophilic emulsifier. Again, homogenization could be carried under high shear homogenization or with a sonication probe. When sonication is used, it must be performed at low power and within a short period of time to not break the first emulsion (Giri et al., 2013). After the formation of the multiple emulsion, evaporation of the volatile organic solvent under low pressure (by a rotary evaporator) or at ambient temperature allows the obtaining of the particulate carriers (Figure 4). There are other types of multiple emulsions like w/o/o or o/w/o (Giri et al., 2013). A lot of parameters may influence the properties of the obtained particles such as, relative phases' ratio (Khoee et al., 2012), amount of the polymer, its nature and molecular weight (Zambaux et al., 1998; Péan et al., 1998; Van de Ven et al., 2011), nature of the surfactants and their amounts (Zhao et al., 2007; Khoee and Yaghoobian, 2009; Dhanaraju et al., 2004), homogenization speed (Eley and Mathew, 2007; Basarkar et al., 2007), the composition of the external phase (Péan et al., 1998; Tse et al., 2009) and evaporation speed (Khoee et al., 2012). Operating conditions may also influence strongly encapsulation efficiency (Tse et al., 2009; Billon et al., 2005; Silva et al., 2013; Zhou et al., 2013; Karataş et al., 2009; Hachicha et al., 2006; Al-Kassas, 2004; Cun et al., 2011; Gaignaux et al., 2012; Cun et al., 2010). Membrane technique and microfluidic devices were also used to prepare particulate carriers by the


DES method (Vladisavljević and Williams, 2008; van der Graaf et al., 2005).

### 3.5 Spray drying


Spray drying is a simple process which gained too much interest due to its cost-effectiveness and scalability (Sou et al., 2011). Practically, a polymer containing drug solution is atomized and sprayed into a drying chamber where droplets are dried by heated air (See Figure 5). Reduction of droplets' size that follows atomization allows the obtaining of an enormous surface area between droplets and the drying gas. The subsequent precipitation of the polymer permits the encapsulation of the drug within the obtained particulate carriers. The evaporation of the solvent occurs within a very short period of time. Consequently, the materials never reach the inlet temperature of drying gas. This is very attractive for encapsulating heat-sensitive drug molecules like proteins (Cal and Sollohub, 2010; Sollohub and Cal, 2010; Prata et al., 2013). Many operating conditions could influence the properties of the obtained particles. Parameters to be controlled include the drying air temperature and humidity (Bruschi et al., 2003), the rate and fluid dynamics of the air flow, the atomization process (Drop-let size, spray rate, spray mechanism) and the composition of ingredients and excipients in the feeding solution (Rattes and Oliveira, 2007). PLA (Baras et al., 2000; Gander et al., 1996; Sastre et al., 2007; Muttill et al., 2007), PLGA (Wang and Wang, 2002; Mu and Feng, 2001; Castelli et al., 1998; Bittner et al., 1999; Prior et al., 2000; Conti et al., 1997), PCL, methacrylate polymers (Esposito et al., 2002; Año et al., 2011; Cruz et al., 2010; Hegazy et al., 2002; Raffin et al., 2008) and chitosan (He et al., 1999; Giunchedi et al., 2002; Cevher et al., 2006) are among the most used polymers in spray-drying method. As Table 6 shows, the technique allowed the obtaining of mainly microparticles bearing better drug solubility and sustained release.

**Table 5:** Applications of the double emulsion technique

Encapsulated molecule	Polymer	Size ( $\mu\text{m}$ )	Zeta potential (mV)	Reference
Vancomycin	PLGA	0.450-0.466	-7.2-(-3.5)	Zakeri-Milani et al., 2013
Prostaglandin E1	PLGA	7-22.5	-	Gupta and Ahsan, 2011
Deoxyribonuclease I	PLGA	0.190-0.349	-	Osman et al., 2011
S. equi antigens	PCL	0.242-0.450	-53.1-38.7	Florindo et al., 2009
Hepatitis B surface antigen	PLGA	1-5	0.51-14	Thomas et al., 2009
Plasmid DNA	PLGA	1.9-4.6	-24.6-(-22.9)	Tse et al., 2009

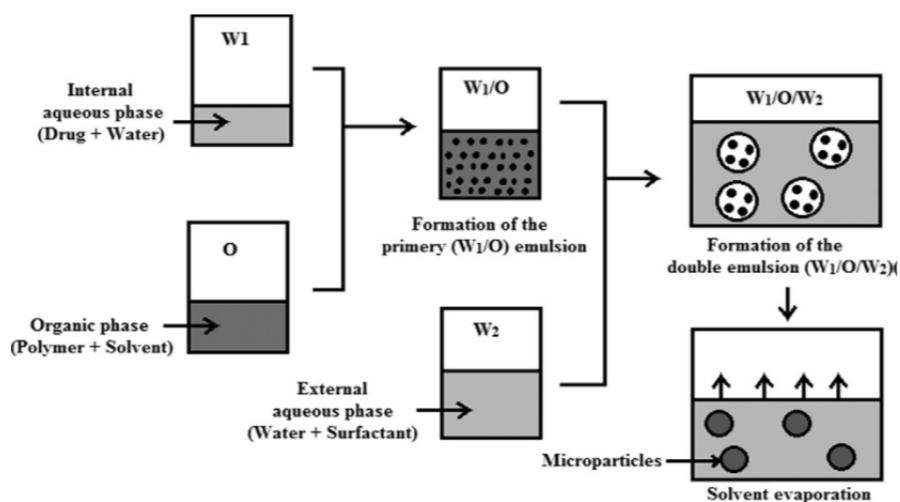

**Figure 4:** Double emulsion solvent evaporation technique (Giri et al., 2013)

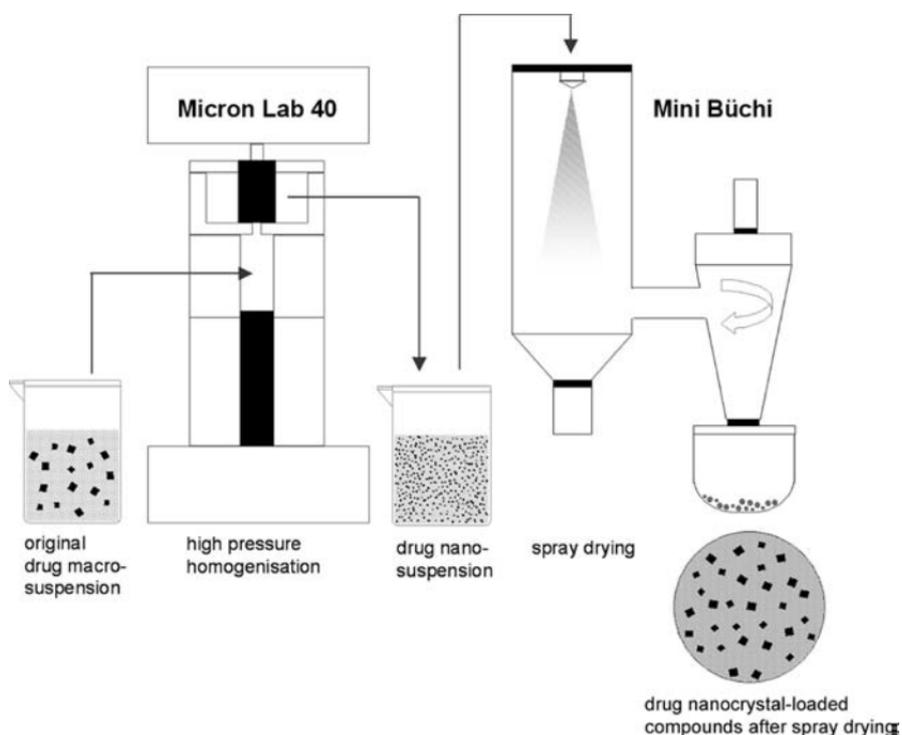

**Figure 5:** The spray drying method (Pinto Reis et al., 2006)

**Table 6:** Applications of the spray drying technique

Encapsulated molecule	Polymer	Size ( $\mu\text{m}$ )	Zeta potential (mV)	Reference
Nimodipine	PLGA	1.9-2.37	-	Bege et al., 2013
Theophylline	Eudragit RS30D	< 60	-	Garekani et al., 2013
Ofloxacin	PLA	2.6-4.9	-	Palazzo et al., 2013
Sodium diclofenac	PGA-co-PDL	2.3	-32.2	Tawfeek, 2013
	PEG-PGA-co-PDL	3.9	-29.9	
	and mPEG-co-(PGA-co-PDL)	2.5	-31.2	
Sodium fluoride	Chitosan	3.4-5.3	-	Keegan et al., 2012
Plasmid	Chitosan	2.5-11.7	-	Mohajel et al., 2012
Heparin	PLGA	2.5-3.8	-63.5 - (-28.2)	Yildiz et al., 2012
Alendronate	Eudragit® S100	13.8	-	Cruz et al., 2010
Zolmitriptan	Chitosan glutamate and Chitosan base	2.6-9.4	-	Alhalaweh et al., 2009
Triamcinolone	PLGA	0.5-1.5	-	da Silva et al., 2009
Acyclovir	Chitosan	18.7-34.9	-	Stulzer et al., 2009

### 3.6 Supercritical fluid technology (SFT)

In the recent years, novel particle formation techniques using supercritical fluids (SCF) have been developed in order to overcome some of the disadvantages of conventional techniques that are: (1) poor control of particle size and morphology; (2) degradation and lost of biological activity of thermo sensitive compounds; (3) low encapsulation efficiency and (4) low precipitation yield (Santos et al., 2013). Moreover, SFT presents the main advantage of not requiring the use of toxic solvents. In fact, SCF based technologies have attracted enormous interest for the production of microparticles and nanoparticles (Table 7), since their emergence in the early 1990s (Sanli et al., 2012).

The supercritical state is achieved when a substance is exposed to conditions above its critical pressure and temperature. In such conditions, the fluid will have liquid-like density and, thus, solvating properties that are similar to those of liquids and, at the same time, gas-like mass transfer properties. Carbon dioxide ( $\text{CO}_2$ ) is the most commonly used critical fluid. In fact,  $\text{CO}_2$  is nontoxic, nonflammable and easy recyclable. Moreover,  $\text{CO}_2$  has moderate critical parameters of  $\text{CO}_2$  (a critical pressure of 7.4

MPa and a critical temperature of 304.1 K) and low price and is highly available which makes it very attractive from an economical point of view and also for the processing of labile compounds (Elizondo et al., 2012). Supercritical fluid technology methods can be divided in four methods which are rapid expansion of supercritical solution (RESS), Particles from gas saturated solutions (PGSS), gas antisolvent (GAS) and supercritical antisolvent process (SAS). These methods depend on whether  $\text{CO}_2$  was used as a solvent, a solute or an antisolvent. Figure 6 shows the experimental set up of the RESS technique. In the RESS technique, the drug and the polymer are first dissolved in supercritical  $\text{CO}_2$  in high pressure chamber. The subsequent passing of the solution through a nozzle results in a rapid decrease of the pressure and thus, a precipitation of the drug particles embedded in the polymer matrix and their recovery in the extraction unit (Byrappa et al., 2008). Many parameters such as the density of the SCF (Pressure and temperature of supercritical fluid) (Kalani and Yunus, 2012), flow rate of drug-polymer solution and/or  $\text{CO}_2$  and formulation variables (Martin et al., 2002) could influence the size of the obtained particles. Table 7 shows that SFT was used for

the processing of nanoparticles and micro-particles mainly based on polyesters.


### 3.7 Ionic gelation (IG)

IG method is used mainly with natural hydrophilic polymers to prepare particulate carriers. These polymers include gelatin, alginate, chitosan and agarose. IG has the advantage of not using organic solvents. The technique is based on the transition of the polymer from liquid state to a gel (Figure 7). For instance, gelatin based particles are obtained after the hardening of the droplets of emulsified gelatin solution. The particles are obtained after cooling gelatin emulsion droplets below the gelation point in an ice bath. For alginate, however, particles are produced by drop-by-drop extrusion of the sodium alginate solution into the


calcium chloride solution. Sodium alginate is, in fact, a water-soluble polymer that gels in the presence of multivalent cations such as calcium. Chitosan particles are prepared by spontaneous formation of complexes between the positively charged chitosan and polyanions (tripolyphosphate or gelatin) or by the gelation of a chitosan solution dispersed in an oil emulsion (Mahapatro and Singh, 2011). Figure 7 illustrates the gelation mechanism of polysaccharides. At high temperatures, a random coil conformation is assumed. With decreasing temperature, the aggregation of double helices structure forms the physical junctions of gels (Rees and Welsh, 1977). Table 8 displays some recent applications of IG. This technique has been mainly used to prepare chitosan nanoparticles.

**Table 7:** Applications of the SCF technology

Encapsulated molecule	Polymer	Size ( $\mu\text{m}$ )	Zeta potential (mV)	Reference
Hydrocortisone acetate	PLGA	1-5	-	Falco et al., 2013
17 $\alpha$ -methyltestosterone	PLA	5.4-20.5	13.9 - 67.7	Sacchetin et al., 2013
Paracetamol	PLA	0.301-1.461	-	Kalani and Yunus, 2012
5-fluorouracil	PLLA-PEG/PEG	0.175	-	Zhang et al., 2012
Human growth hormone	PLGA	93	-	Jordan et al., 2010
Azacytidine	PLA	2	-	Argemí et al., 2009
Bovine serum albumin	PLA	2.5	-	Kang et al., 2009
Retinyl palmitate	PLA	0.040-0.110	-	Sane and Limtrakul, 2009
Indomethacin	PLA	2.35	-	Kang et al., 2008

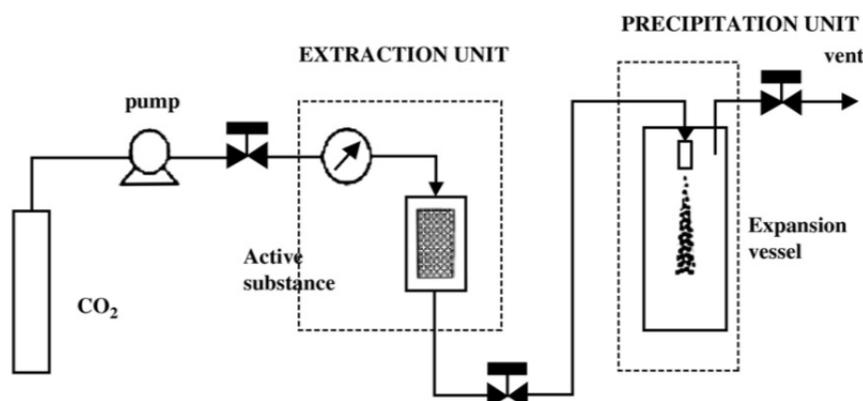

**Figure 6:** Schematic presentation of the experimental set up for the RESS process (Byrappa et al., 2008)

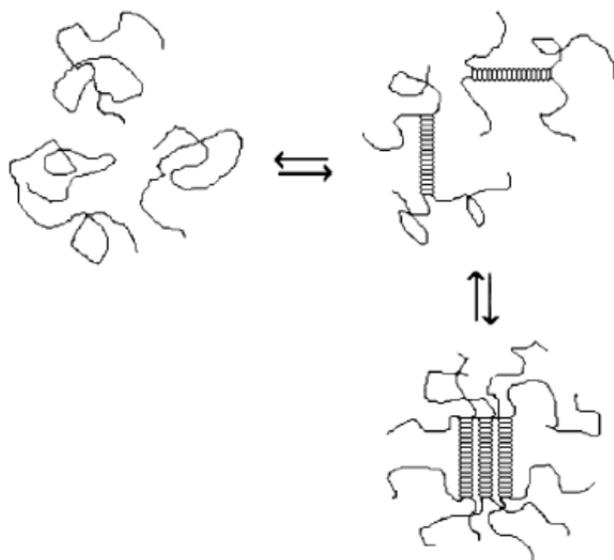

**Figure 7:** Gelation mechanism of polysaccharides in water (Guenet, 1992)

**Table 8:** Some applications of the ionic gelation technique

Encapsulated molecule	Polymer	Size ( $\mu\text{m}$ )	Zeta potential (mV)	Reference
Articaine hydrochloride	Alginate/chitosan	0.340-0.550	-22 - (-19)	de Melo et al., 2013
TNF- $\alpha$ siRNA	Trimethyl chitosan-cysteine	0.146	25.9	He et al., 2013
Paclitaxel	O-carboxymethyl chitosan	0.130-0.180	-30 - (-12)	Maya et al., 2013
pDNA	Chitosan	0.153-0.403	46.2-56.9	Cadete et al., 2012
Gemcitabine	Chitosan	0.095	-	Derakhshandeh and Fathi, 2012
Dexamthasone sodium phosphate	Chitosan	0.256-0.350	-	Doustgani et al., 2012
Itraconazole	Chitosan	0.190-0.240	11.5-18.9	Jafarinejad et al., 2012
5-fluorouracil and leucovorin	Chitosan	0.040-0.097	25.6-28.9	Li et al., 2011
Insulin	Chitosan and arabic gum	0.172-0.245	35.7-43.4	Avadi et al., 2010
CKS9 peptide sequence	Chitosan	0.226	-	Yoo et al., 2010


### 3.8 Layer by layer

Polyelectrolyte self assembly is also called layer-by-layer (LbL) assembly process. The earliest technology was based on the assembly of colloidal particles on a solid core (Iler, 1966). From the 1990s, applications were expanded. LbL allowed, in fact, the assembly of polyelectrolyte films using biopolymers, proteins, peptides, poly-

saccharides and DNA (Powell et al., 2011). This approach was first developed by Sukhorukov et al. (Sukhorukov et al., 1998). Polyelectrolytes are classified according to their origin. Standard synthetic polyelectrolytes include poly(styrene sulfonate) (PSS), poly(dimethyldiallylammonium chloride) (PDDA), poly(ethylenimine) (PEI), poly(N-isopropyl acrylamide) (PNIPAM), poly-

(acrylic acid) (PAA), poly (methacrylic acid) (PMA), poly(vinyl sulfate) (PVS) and poly(allylamine) (PAH). Natural polyelectrolytes include nucleic acids, proteins and polysaccharides such as, alginic acid, chondroitin sulfate, DNA, heparin, chitosan, cellulose sulfate, dextran sulfate and carboxymethylcellulose (de Villiers et al., 2011). The obtained particles are vesicular and are called polyelectrolyte capsules. Assembly process is based on irreversible electrostatic attraction that leads to polyelectrolyte adsorption at supersaturating polyelectrolyte concentrations. Other interactions such as, hydrogen bonds, hydrophobic interactions and Van der Waals forces were also described (de Villiers et al., 2011). A colloidal template that serves to the adsorption of the polyelectrolyte is also needed. The commonly used cores for the formulated particles are derived from stabilized colloidal dispersions of charged silica, charged poly(styrene) spheres, metal oxides, polyoxometalates and conducting liquid crystalline polymers. Carrier systems can be functionalized with stimuli-responsive components that respond to temperature, pH and

ionic strength. The polymers/colloids used in LbL technique can also be functionalized to alter their properties preceding layer by layer assembly. Experimental parameters that have to be managed include coating material concentration, ion concentration and the pH of the medium (Vergaro et al., 2011). Polymer assembly occurs after incubation of the template in the polymer solution or by decreasing polymer solubility by drop-wise addition of a miscible solvent (Radtchenko et al., 2002). This procedure could be repeated with a second polymer to allow sequential deposition of multiple polymer layers (Figure 8). LbL presents advantages over several conventional coating methods: (1) simplicity of the process and equipment; (2) its suitability for coating most surfaces; (3) availability and abundance of natural and synthetic colloids; (4) flexible application to objects with irregular shapes and sizes; (5) formation of stabilizing coats and (6) control over the required multilayer thickness (de Villiers et al., 2011). Table 9 contains some recent applications of LbL technique.

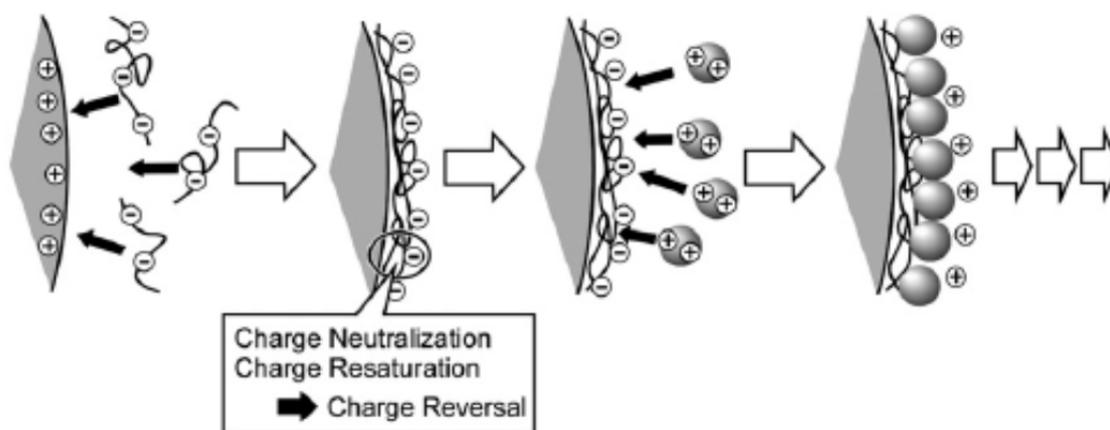

**Figure 8:** The layer by layer technique based on electrostatic interaction (Ariga et al., 2011)

**Table 9:** Applications of the layer-by-layer technique

Active	Polyelectrolytes	Size (µm)	Zeta potential (mV)	References
Kaempferol	Sodium Alginate and protamine sulfate	0.161	- 8.9	Kumar et al., 2012
Designed peptide DP-2015	Poly-L-glutamic acid and poly-L-lysine	-	-	Powell et al., 2011
5-fluorouracil	Poly(L-glutamic acid) and chitosan	1	25-40	Yan et al., 2011
Plasmid DNA	Plasmid DNA and reducible hyperbranched poly(amidoamine) or polyethylenimine	-	-	Blacklock et al., 2009
Artemisinin	Alginate, gelatin and chitosan	0.806	-33	Chen et al., 2009
Insulin	Glucose oxidase and catalase	6	-	Qi et al., 2009
Heparin	Poly(styrene sulfonate) and chitosan	1	-10.4	Shao et al., 2009
Acyclovir	Poly(vinyl galactose ester-co-methacryloxyethyl trimethylammonium chloride) and poly(sodium 4-styrenesulfonate)	-	-	Zhang et al., 2008a
Propranolol hydrochloride	Poly(vinyl galactose ester-co-methacryloxyethyl trimethylammonium chloride) and Poly(sodium 4-styrenesulfonate)	5-15.6	-	Zhang et al., 2008b

## CONCLUSION

Encapsulation of active molecules is a crucial approach that has been widely used for many biomedical applications. It permits enhancement of bioavailability of molecules, sustained delivery, passive or active targeting and decrease of toxicity and side effects. These formulations can render some active molecules more suitable for a specific route such as the delivery of proteins by the oral route or the delivery of some drugs via the blood brain barrier. Thus, they enhance efficiency, patient compliance and allow successful management of diseases. Many biodegradable and biocompatible polymers were investigated. The choice of the technique and the suitable polymer is a crucial step. It depends on the physicochemical properties of the drug to be encapsulated. The management of operating conditions is also a hard task to monitor particles' properties and to enhance drug loading. Recent research works are focus-

ing on active targeting by the coating the carriers by biomolecules that specifically recognize a well-defined cell receptor. One can also notice a shift for more 'intelligent' drug delivery systems. Responsive materials, for example, react to a specific physiological stimulus such as a variation of pH to release the encapsulated drug. Other thermo-sensitive materials deliver drugs at a specific temperature. It can be noted also that more attention is paid to safer methods that avoid the use of organic solvents (RESS) or to techniques that provide better reproducibility and easy scalability (microfluidics and membrane emulsification technology), which could be attractive for industrial processing.

## REFERENCES

- Adibkia K, Javadzadeh Y, Dastmalchi S, Mohammadi G, Niri FK, Alaei-Beirami M. Naproxen-eudragit rs100 nanoparticles: preparation and physicochemical characterization. *Colloids Surf B Biointerfaces* 2011;83:155–9.
- Agnihotri SM, Vavia PR. Drug loaded poly[lac(glc-leu)] microparticles: formulation and release characteristics. *Colloids Surf B Biointerfaces* 2009;74:336–9.
- Ahmad H. A special issue on polymer and hybrid particles for biomedical applications. *J Colloid Sci Biotechnol* 2013;2:153–4.
- Al-Kassas R. Design and in vitro evaluation of gentamicin-eudragit microspheres intended for intra-ocular administration. *J Microencapsul* 2004;21:71–81.
- Alhalaweh A, Andersson S, Velaga SP. Preparation of zolmitriptan-chitosan microparticles by spray drying for nasal delivery. *Eur J Pharm Sci* 2009;38:206–14.
- Almouazen E, Bourgeois S, Boussaïd A, Valot P, Mallevall C et al. Development of a nanoparticle-based system for the delivery of retinoic acid into macrophages. *Int J Pharm* 2012;430:207–15.
- Alpar HO, Somavarapu S, Atuah KN, Bramwell VW. Biodegradable mucoadhesive particulates for nasal and pulmonary antigen and dna delivery. *Adv Drug Deliv Rev* 2005;57:411–30.
- Año G, Esquisabel A, Pastor M, Talavera A, Cedré B et al. A new oral vaccine candidate based on the microencapsulation by spray-drying of inactivated vibrio cholerae. *Vaccine* 2011;29:5758–64.
- Argemí A, Vega A, Subra-Paternault P, Saurina J. Characterization of azacytidine/poly(l-lactic) acid particles prepared by supercritical antisolvent precipitation. *J Pharm Biomed Anal* 2009;50:847–52.
- Arias JL, López-Viota M, Sáez-Fernández E, Ruiz MA. Formulation and physicochemical characterization of poly( $\epsilon$ -caprolactone) nanoparticles loaded with fltorafur and diclofenac sodium. *Colloids Surf B Biointerfaces* 2010;75:204–8.
- Ariga K, Lvov YM, Kawakami K, Ji Q, Hill JP. Layer-by-layer self-assembled shells for drug delivery. *Adv Drug Deliv Rev* 2011;63:762–71.
- Asada M, Takahashi H, Okamoto H, Tanino H, Danjo K. Theophylline particle design using chitosan by the spray drying. *Int J Pharm* 2004;270:167–74.
- Asadi H, Rostamizadeh K, Salari D, Hamidi M. Preparation of biodegradable nanoparticles of triblock pla-peg-pla copolymer and determination of factors controlling the particle size using artificial neural network. *J Microencapsul* 2011;28:406–16.
- Ataman-Önal Y, Munier S, Ganée A, Terrat C, Durand P-Y et al. Surfactant-free anionic pla nanoparticles coated with hiv-1 p24 protein induced enhanced cellular and humoral immune responses in various animal models. *J Control Release* 2006;112:175–85.
- Aumelas A, Serrero A, Durand A, Dellacherie E, Leonard M. Nanoparticles of hydrophobically modified dextrans as potential drug carrier systems. *Colloids Surf B Biointerfaces* 2007;59:74–80.
- Avachat AM, Bornare PN, Dash RR. Sustained release microspheres of ropinirole hydrochloride: effect of process parameters. *Acta Pharm Zagreb Cro-at* 2011;61:363–76.
- Avadi MR, Sadeghi AMM, Mohammadpour N, Abedin S, Atyabi F et al. Preparation and characterization of insulin nanoparticles using chitosan and arabic gum with ionic gelation method. *Nanomed Nanotechnol Biol Med* 2010;6:58–63.
- Balthasar S, Michaelis K, Dinauer N, von Briesen H, Kreuter J, Langer K. Preparation and characterisation of antibody modified gelatin nanoparticles as drug carrier system for uptake in lymphocytes. *Biomaterials* 2005;26:2723–32.
- Banerjee P, Deb J, Roy A, Ghosh A, Chakraborty P. Fabrication and development of pectin microsphere of metformin hydrochloride. *ISRN Pharm* 2012;230621. doi: 10.5402/2012/230621.
- Baras B, Benoit M-A, Gillard J. Parameters influencing the antigen release from spray-dried poly(dl-lactide) microparticles. *Int J Pharm* 2000;200:133–45.
- Basarkar A, Devineni D, Palaniappan R, Singh J. Preparation, characterization, cytotoxicity and transfection efficiency of poly(dl-lactide-co-glycolide) and poly(dl-lactic acid) cationic nanoparticles for controlled delivery of plasmid dna. *Int J Pharm* 2007;343:247–54.

- Bazylińska U, Lewińska A, Lamch Ł, Wilk KA. Polymeric nanocapsules and nanospheres for encapsulation and long sustained release of hydrophobic cyanine-type photosensitizer. *Colloids Surf Physicochem Eng Asp* 2013.
- Beck-Broichsitter M, Ruppert C, Schmehl T, Guenther A, Betz T et al. Biophysical investigation of pulmonary surfactant surface properties upon contact with polymeric nanoparticles in vitro. *Nanomed Nanotechnol Biol Med* 2011;7:341–50.
- Beck-Broichsitter M, Schweiger C, Schmehl T, Gessler T, Seeger W, Kissel T. Characterization of novel spray-dried polymeric particles for controlled pulmonary drug delivery. *J Control Release* 2012; 158:329–35.
- Bege N, Renette T, Endres T, Beck-Broichsitter M, Hänggi D, Kissel T. In situ forming nimodipine depot system based on microparticles for the treatment of posthemorrhagic cerebral vasospasm. *Eur J Pharm Biopharm* 2013;84:99–105.
- Behera T, Swain P. Antigen adsorbed surface modified poly- $\epsilon$ -caprolactone microspheres stimulates both adaptive and innate immune response in fish. *Vaccine* 2012;30:5278–84.
- Benoit MA, Baras B, Gillard J. Preparation and characterization of protein-loaded poly( $\epsilon$ -caprolactone) microparticles for oral vaccine delivery. *Int J Pharm* 1999;184:73–84.
- Bernkop-Schnürch A, Heinrich A, Greimel A. Development of a novel method for the preparation of submicron particles based on thiolated chitosan. *Eur J Pharm Biopharm* 2006;63:166–72.
- Bilati U, Allémann E, Doelker E. Development of a nanoprecipitation method intended for the entrapment of hydrophilic drugs into nanoparticles. *Eur J Pharm Sci* 2005;24:67–75.
- Billon A, Chabaud L, Gouyette A, Bouler J-M, Merle C. Vancomycin biodegradable poly(lactide-co-glycolide) microparticles for bone implantation. influence of the formulation parameters on the size, morphology, drug loading and in vitro release. *J Microencapsul* 2005;22:841–52.
- Bittner B, Mäder K, Kroll C, Borchert H-H, Kissel T. Tetracycline-hcl-loaded poly(dl-lactide-co-glycolide) microspheres prepared by a spray drying technique: influence of  $\gamma$ -irradiation on radical formation and polymer degradation. *J Control Release* 1999; 59:23–32.
- Blacklock J, You Y-Z, Zhou Q-H, Mao G, Oupický D. Gene delivery in vitro and in vivo from bio-reducible multilayered polyelectrolyte films of plasmid dna. *Biomaterials* 2009;30:939–50.
- Bozkir A, Saka OM. Formulation and investigation of 5-fu nanoparticles with factorial design-based studies. *Il Farm* 2005;60:840–6.
- Bruschi M, Cardoso ML, Lucchesi M, Gremião MP. Gelatin microparticles containing propolis obtained by spray-drying technique: preparation and characterization. *Int J Pharm* 2003;264:45–55.
- Budhian A, Siegel SJ, Winey KI. Haloperidol-loaded plga nanoparticles: systematic study of particle size and drug content. *Int J Pharm* 2007;336: 367–75.
- Byrappa K, Ohara S, Adschiri T. Nanoparticles synthesis using supercritical fluid technology - towards biomedical applications. *Adv Drug Deliv Rev* 2008; 60:299–327.
- Cadete A, Figueiredo L, Lopes R, Calado CCR, Almeida AJ, Gonçalves LMD. Development and characterization of a new plasmid delivery system based on chitosan-sodium deoxycholate nanoparticles. *Eur J Pharm Sci* 2012;45:451–8.
- Cal K, Sollohub K. Spray drying technique. i: hardware and process parameters. *J Pharm Sci* 2010;99: 575–86.
- Campos EVR, de Melo NFS, de Paula E, Rosa AH, Fraceto LF. Screening of conditions for the preparation of poly( $\epsilon$ -caprolactone) nanocapsules containing the local anesthetic articaine. *J Colloid Sci Biotechnol* 2013;2:106–11.
- Castelli F, Conti B, Maccarrone DE, Conte U, Puglisi G. Comparative study of 'in vitro' release of anti-inflammatory drugs from polylactide-co-glycolide microspheres. *Int J Pharm* 1998;176:85–98.
- Cevher E, Orhan Z, Mülazımoğlu L, Şensoy D, Alper M et al. Characterization of biodegradable chitosan microspheres containing vancomycin and treatment of experimental osteomyelitis caused by methicillin-resistant staphylococcus aureus with prepared microspheres. *Int J Pharm* 2006;317:127–35.
- Challa R, Ahuja A, Ali J, Khar RK. Cyclodextrins in drug delivery: an updated review. *AAPS Pharm Sci Tech* 2005;6:E329–57.

- Chawla JS, Amiji MM. Biodegradable poly( $\epsilon$ -caprolactone) nanoparticles for tumor-targeted delivery of tamoxifen. *Int J Pharm* 2002;249:127–38.
- Chen A-Z, Zhao Z, Wang S-B, Li Y, Zhao C, Liu Y-G. A continuous res process to prepare pla-peg-pla microparticles. *J Supercrit Fluids* 2011;59:92–7.
- Chen Y, Lin X, Park H, Greever R. Study of artemisinin nanocapsules as anticancer drug delivery systems. *Nanomed Nanotechnol Biol Med* 2009;5:316–22.
- Chorny M, Fishbein I, Danenberg HD, Golomb G. Lipophilic drug loaded nanospheres prepared by nanoprecipitation: effect of formulation variables on size, drug recovery and release kinetics. *J Control Release* 2002;83:389–400.
- Çirpanlı Y, Bilensoy E, Lale Doğan A, Çalış S. Comparative evaluation of polymeric and amphiphilic cyclodextrin nanoparticles for effective camptothecin delivery. *Eur J Pharm Biopharm* 2009;73:82–9.
- Çirpanlı Y, Allard E, Passirani C, Bilensoy E, Lemaire L et al. Antitumoral activity of camptothecin-loaded nanoparticles in 9l rat glioma model. *Int J Pharm* 2011;403:201–6.
- Cohen-Sela E, Chorny M, Koroukhov N, Danenberg HD, Golomb G. A new double emulsion solvent diffusion technique for encapsulating hydrophilic molecules in plga nanoparticles. *J Control Release* 2009;133:90–5.
- Contado C, Vighi E, Dalpiaz A, Leo E. Influence of secondary preparative parameters and aging effects on plga particle size distribution: a sedimentation field flow fractionation investigation. *Anal Bioanal Chem* 2013;405:703–11.
- Conti B, Bucolo C, Giannavola C, Puglisi G, Giunchedi P, Conte U. Biodegradable microspheres for the intravitreal administration of acyclovir: in vitro/in vivo evaluation. *Eur J Pharm Sci* 1997;5:287–93.
- Cruz L, Assumpção E, Andrade SF, Conrado DJ, Kulkamp IC et al. Gastroresistant microparticles containing sodium alendronate prevent the bone loss in ovariectomized rats. *Eur J Pharm Sci* 2010;40:441–7.
- Cun D, Foged C, Yang M, Frøkjær S, Nielsen HM. Preparation and characterization of poly(d,l-lactide-co-glycolide) nanoparticles for sirna delivery. *Int J Pharm* 2010;390:70–5.
- Cun D, Jensen DK, Maltesen MJ, Bunker M, Whiteside P et al. High loading efficiency and sustained release of sirna encapsulated in plga nanoparticles: quality by design optimization and characterization. *Eur J Pharm Biopharm* 2011;77:26–35.
- D'Aurizio E, van Nostrum CF, van Steenberg MJ, Sozio P, Siepmann F et al. Preparation and characterization of poly(lactic-co-glycolic acid) microspheres loaded with a labile antiparkinson prodrug. *Int J Pharm* 2011;409:289–96.
- Da Silva AA Jr, de Matos JR, Formariz TP, Rossanezi G, Scarpa MV et al. Thermal behavior and stability of biodegradable spray-dried microparticles containing triamcinolone. *Int J Pharm* 2009;368:45–55.
- Dai C, Wang Y, Hou X. Preparation and protein adsorption of porous dextran microspheres. *Carbohydr Polym* 2012;87:2338–43.
- Dai M, Xu X, Song J, Fu S, Gou M et al. Preparation of camptothecin-loaded phec microspheres for the treatment of colorectal peritoneal carcinomatosis and tumor growth in mice. *Cancer Lett* 2011;312:189–96.
- Danhier F, Ansorena E, Silva JM, Coco R, Le Breton A, Préat V. Plga-based nanoparticles: an overview of biomedical applications. *J Control Release* 2012;161:505–22.
- Das S, Suresh PK, Desmukh R. Design of eudragit rl 100 nanoparticles by nanoprecipitation method for ocular drug delivery. *Nanomed Nanotechnol Biol Med* 2010;6:318–23.
- Dash TK, Konkimalla VB. Poly- $\epsilon$ -caprolactone based formulations for drug delivery and tissue engineering: a review. *J Control Release* 2012;158:15–33.
- De Melo NFS, Campos EVR, de Paula E, Rosa AH, Fraceto LF. Factorial design and characterization studies for articaine hydrochloride loaded alginate/chitosan nanoparticles. *J Colloid Sci Biotechnol* 2013;2:146–52.
- De Villiers MM, Otto DP, Strydom SJ, Lvov YM. Introduction to nanocoatings produced by layer-by-layer (lbl) self-assembly. *Adv Drug Deliv Rev* 2011;63:701–15.
- Delie F, Berton M, Allémann E, Gurny R. Comparison of two methods of encapsulation of an oligonucleotide into poly(d,l-lactic acid) particles. *Int J Pharm* 2001;214:25–30.

- Derakhshandeh K, Fathi S. Role of chitosan nanoparticles in the oral absorption of gemcitabine. *Int J Pharm* 2012;437:172–7.
- Devissaguet J-P, Fessi H, Puisieux F. Process for the preparation of dispersible colloidal systems of a substance in the form of nanocapsules. US Patent 5049322, 1991.
- Dhanaraju MD, Jayakumar R, Vamsadhara C. Influence of manufacturing parameters on development of contraceptive steroid loaded injectable microspheres. *Chem Pharm Bull (Tokyo)* 2004;52:976–9.
- Dinarvand R, Sepehri N, Manoochehri S, Rouhani H, Atyabi F. Poly(lactide-co-glycolide) nanoparticles for controlled delivery of anticancer agents. *Int J Nanomed* 2011;6:877–95.
- Doan TVP, Couet W, Olivier JC. Formulation and in vitro characterization of inhalable rifampicin-loaded PLGA microspheres for sustained lung delivery. *Int J Pharm* 2011;414:112–7.
- Dong Y, Feng SS. Methoxy poly(ethylene glycol)-poly(lactide) (mPEG-PLA) nanoparticles for controlled delivery of anticancer drugs. *Biomaterials* 2004;25:2843–9.
- Dong Y, Feng SS. In vitro and in vivo evaluation of methoxy poly(ethylene glycol)-poly(lactide) (mPEG-PLA) nanoparticles for small-molecule drug chemotherapy. *Biomaterials* 2007;28:4154–60.
- Doustgani A, Farahani EV, Imani M, Doulabi AH. Dexamethasone sodium phosphate release from chitosan nanoparticles prepared by ionic gelation method. *J Colloid Sci Biotechnol* 2012;1:42–50.
- Du W-L, Niu S-S, Xu Y-L, Xu Z-R, Fan C-L. Antibacterial activity of chitosan tripolyphosphate nanoparticles loaded with various metal ions. *Carbohydr Polym* 2009;75:385–9.
- Duchêne D. Cyclodextrins in targeting application to nanoparticles. *Adv Drug Deliv Rev* 1999;36:29–40.
- Duchêne D, Ponchel G, Wouessidjewe D. Cyclodextrins in targeting: application to nanoparticles. *Adv Drug Deliv Rev* 1999;36:29–40.
- Eidi H, Joubert O, Attik G, Duval RE, Bottin MC et al. Cytotoxicity assessment of heparin nanoparticles in NR8383 macrophages. *Int J Pharm* 2010;396:156–65.
- Elaissari A. Thermally sensitive latex particles. In: Birdi K (ed.): *Handbook of surface and colloid chemistry*, 2<sup>nd</sup> ed. Boca Raton, FL: CRC Press, 2002.
- Eley JG, Mathew P. Preparation and release characteristics of insulin and insulin-like growth factor-one from polymer nanoparticles. *J Microencapsul* 2007;24:225–34.
- Elias H-G. *An introduction to plastics*. Weinheim: Wiley-VCH, 2003.
- Elizondo E, Veciana J, Ventosa N. Nanostructuring molecular materials as particles and vesicles for drug delivery, using compressed and supercritical fluids. *Nanomedicine* 2012;7:1391–1408.
- Elmizadeh H, Khanmohammadi M, Ghasemi K, Hassanzadeh G, Nassiri-Asl M, Garmarudi AB. Preparation and optimization of chitosan nanoparticles and magnetic chitosan nanoparticles as delivery systems using Box-Behnken statistical design. *J Pharm Biomed Anal* 2013;80:141–6.
- Esmaeili A, Saremnia B, Koohian A, Rezazadeh S. Mechanism of nanocapsules of Matricaria recutita L. extract formation by the emulsion-diffusion process. *Superlattices Microstruct* 2011;50:340–9.
- Esposito E, Cervellati F, Menegatti E, Nastruzzi C, Cortesi R. Spray dried Eudragit microparticles as encapsulation devices for vitamin C. *Int J Pharm* 2002;242:329–34.
- Essa S, Rabanel JM, Hildgen P. Effect of aqueous solubility of grafted moiety on the physicochemical properties of poly(D,L-lactide) (PLA) based nanoparticles. *Int J Pharm* 2010;388:263–73.
- Fàbregas A, Miñarro M, García-Montoya E, Pérez-Lozano P, Carrillo C et al. Impact of physical parameters on particle size and reaction yield when using the ionic gelation method to obtain cationic polymeric chitosan-tripolyphosphate nanoparticles. *Int J Pharm* 2013;446:199–204.
- Falamazian A, Lavasanifar A. Optimization of the hydrophobic domain in poly(ethylene oxide)-poly( $\epsilon$ -caprolactone) based nano-carriers for the solubilization and delivery of amphotericin B. *Colloids Surf B Biointerfaces* 2010;81:313–20.
- Falco N, Reverchon E, Della Porta G. Injectable PLGA/hydrocortisone formulation produced by continuous supercritical emulsion extraction. *Int J Pharm* 2013;441:589–97.

- Florindo HF, Pandit S, Lacerda L, Gonçalves LMD, Alpar HO, Almeida AJ. The enhancement of the immune response against s. equi antigens through the intranasal administration of poly- $\epsilon$ -caprolactone-based nanoparticles. *Biomaterials* 2009;30:879–91.
- Fonseca C, Simões S, Gaspar R. Paclitaxel-loaded plga nanoparticles: preparation, physicochemical characterization and in vitro anti-tumoral activity. *J Control Release* 2002;83:273–86.
- Fredriksen BN, Grip J. Plga/pla micro- and nanoparticle formulations serve as antigen depots and induce elevated humoral responses after immunization of atlantic salmon (*salmo salar* l.). *Vaccine* 2012;30:656–67.
- Gaignaux A, Réeff J, Siepmann F, Siepmann J, De Vriese C et al. Development and evaluation of sustained-release clonidine-loaded plga microparticles. *Int J Pharm* 2012;437:20–8.
- Galindo-Rodríguez SA, Puel F, Briçon S, Al-lémann E, Doelker E, Fessi H. Comparative scale-up of three methods for producing ibuprofen-loaded nanoparticles. *Eur J Pharm Sci* 2005;25:357–67.
- Gan Q, Wang T, Cochrane C, McCarron P. Modulation of surface charge, particle size and morphological properties of chitosan–tpp nanoparticles intended for gene delivery. *Colloids Surf B Biointerfaces* 2005;44:65–73.
- Gander B, Johansen P, Nam-Trân H, Merkle HP. Thermodynamic approach to protein microencapsulation into poly(d,l-lactide) by spray drying. *Int J Pharm* 1996;129:51–61.
- Garekani HA, Moghaddam ZF, Sadeghi F. Organic solution versus aqueous dispersion of eudragit rs in preparation of sustained release microparticles of theophylline using spray drying. *Colloids Surf B Biointerfaces* 2013;108:374–9.
- Gennes P-G. *Scaling concepts in polymer physics*. Ithaca, NY: Cornell University Press, 197.
- Gèze A, Aous S, Baussanne I, Putaux J, Defaye J, Wouessidjewe D. Influence of chemical structure of amphiphilic  $\beta$ -cyclodextrins on their ability to form stable nanoparticles. *Int J Pharm* 2002;242:301–5.
- Giri TK, Choudhary C, Ajazuddin, Alexander A, Badwaik H, Tripathi DK. Prospects of pharmaceuticals and biopharmaceuticals loaded microparticles prepared by double emulsion technique for controlled delivery. *Saudi Pharm J* 2013;21:125–41.
- Giunchedi P, Juliano C, Gavini E, Cossu M, Sorrenti M. Formulation and in vivo evaluation of chlorhexidine buccal tablets prepared using drug-loaded chitosan microspheres. *Eur J Pharm Biopharm* 2002;53:233–9.
- Gou M, Zheng L, Peng X, Men K, Zheng X et al. Poly( $\epsilon$ -caprolactone)–poly(ethylene glycol)–poly( $\epsilon$ -caprolactone) (pcl–peg–pcl) nanoparticles for honokiol delivery in vitro. *Int J Pharm* 2009;375:170–6.
- Govender T, Stolnik S, Garnett MC, Illum L, Davis SS. Plga nanoparticles prepared by nanoprecipitation: drug loading and release studies of a water soluble drug. *J Control Release* 1999;57:171–85.
- Govender T, Riley T, Ehtezazi T, Garnett MC, Stolnik S et al. Defining the drug incorporation properties of pla–peg nanoparticles. *Int J Pharm* 2000;199:95–110.
- Guenet J-M. *Thermoreversible gelation of polymers and biopolymers*. New York: Academic Press, 1992.
- Guerreiro LH, Da Silva D, Ricci-Junior E, Girard-Dias W, Mascarenhas CM et al. Polymeric particles for the controlled release of human amylin. *Colloids Surf B Biointerfaces* 2012;94:101–6.
- Gupta AP, Kumar V. New emerging trends in synthetic biodegradable polymers – polylactide: a critique. *Eur Polym J* 2007;43:4053–74.
- Gupta V, Ahsan F. Influence of pei as a core modifying agent on plga microspheres of pge<sub>1</sub>, a pulmonary selective vasodilator. *Int J Pharm* 2011;413:51–62.
- Gyulai G, Péntes CB, Mohai M, Csémpesz F, Kiss É. Influence of surface properties of polymeric nanoparticles on their membrane affinity. *Eur Polym J* 2013;49:2495–503.
- Hachicha W, Kodjikian L, Fessi H. Preparation of vancomycin microparticles: importance of preparation parameters. *Int J Pharm* 2006;324:176–84.
- Han S, Li M, Liu X, Gao H, Wu Y. Construction of amphiphilic copolymer nanoparticles based on gelatin as drug carriers for doxorubicin delivery. *Colloids Surf B Biointerfaces* 2013;102:833–41.
- Hao S, Wang B, Wang Y, Zhu L, Wang B, Guo T. Preparation of eudragit l 100-55 enteric nanoparticles by a novel emulsion diffusion method. *Colloids Surf B Biointerfaces* 2013;108:127–33.

- Haznedar S, Dortunç B. Preparation and in vitro evaluation of eudragit microspheres containing acetazolamide. *Int J Pharm* 2004;269:131–40.
- He P, Davis SS, Illum L. Chitosan microspheres prepared by spray drying. *Int J Pharm* 1999;187:53–65.
- He C, Yin L, Tang C, Yin C. Multifunctional polymeric nanoparticles for oral delivery of tnf- $\alpha$  sirna to macrophages. *Biomaterials* 2013;34:2843–54.
- Hegazy N, Demirel M, Yazan Y. Preparation and in vitro evaluation of pyridostigmine bromide microparticles. *Int J Pharm* 2002;242:171–4.
- Hernán Pérez de la Ossa D, Ligresti A, Gil-Alegre ME, Aberturas MR, Molpeceres J et al. Poly- $\epsilon$ -caprolactone microspheres as a drug delivery system for cannabinoid administration: development, characterization and in vitro evaluation of their antitumoral efficacy. *J Control Release* 2012;161:927–32.
- Hombreiro Pérez M, Zinutti C, Lamprecht A, Ubrich N, Astier A et al. The preparation and evaluation of poly( $\epsilon$ -caprolactone) microparticles containing both a lipophilic and a hydrophilic drug. *J Control Release* 2000;65:429–38.
- Hu Y, Jiang X, Ding Y, Zhang L, Yang C et al. Preparation and drug release behaviors of nimodipine-loaded poly(caprolactone)-poly(ethylene oxide)-polylactide amphiphilic copolymer nanoparticles. *Biomaterials* 2003;24:2395–404.
- Huang Y-Y, Chung T-W, Tzeng T. Drug release from pla/peg microparticulates. *Int J Pharm* 1997;156:9–15.
- Huang Y, Gao H, Gou M, Ye H, Liu Y et al. Acute toxicity and genotoxicity studies on poly( $\epsilon$ -caprolactone)-poly(ethylene glycol)-poly( $\epsilon$ -caprolactone) nanomaterials. *Mutat Res Toxicol Environ Mutagen* 2010;696:101–6.
- Hyvönen S, Peltonen L, Karjalainen M, Hirvonen J. Effect of nanoprecipitation on the physicochemical properties of low molecular weight poly(l-lactic acid) nanoparticles loaded with salbutamol sulphate and beclomethasone dipropionate. *Int J Pharm* 2005;295:269–81.
- Iler RK. Multilayers of colloidal particles. *J Colloid Interface Sci* 1966;21:569–94.
- Illum L, Fisher AN, Jabbal-Gill I, Davis SS. Bioadhesive starch microspheres and absorption enhancing agents act synergistically to enhance the nasal absorption of polypeptides. *Int J Pharm* 2001;222:109–19.
- Ishihara T, Takahashi M, Higaki M, Mizushima Y, Mizushima T. Preparation and characterization of a nanoparticulate formulation composed of peg-pla and pla as anti-inflammatory agents. *Int J Pharm* 2010;385:170–5.
- Jafarnejad S, Gilani K, Moazeni E, Ghazi-Khansari M, Najafabadi AR, Mohajel N. Development of chitosan-based nanoparticles for pulmonary delivery of itraconazole as dry powder formulation. *Powder Technol* 2012;222:65–70.
- Jain AK, Swarnakar NK, Godugu C, Singh RP, Jain S. The effect of the oral administration of polymeric nanoparticles on the efficacy and toxicity of tamoxifen. *Biomaterials* 2011;32:503–15.
- Javadzadeh Y, Ahadi F, Davaran S, Mohammadi G, Sabzevari A, Adibkia K. Preparation and physicochemical characterization of naproxen-plga nanoparticles. *Colloids Surf B Biointerfaces* 2010;81:498–502.
- Jordan F, Naylor A, Kelly CA, Howdle SM, Lewis A, Illum L. Sustained release hgh microsphere formulation produced by a novel supercritical fluid technology: in vivo studies. *J Control Release* 2010;141:153–60.
- Kadam RS, Tyagi P, Edelhauser HF, Kompella UB. Influence of choroidal neovascularization and biodegradable polymeric particle size on transscleral sustained delivery of triamcinolone acetate. *Int J Pharm* 2012;434:140–7.
- Kalani M, Yunus R. Effect of supercritical fluid density on nanoencapsulated drug particle size using the supercritical antisolvent method. *Int J Nanomed* 2012;7:2165–72.
- Kang Y, Wu J, Yin G, Huang Z, Yao Y et al. Preparation, characterization and in vitro cytotoxicity of indomethacin-loaded plla/plga microparticles using supercritical co2 technique. *Eur J Pharm Biopharm* 2008;70:85–97.
- Kang Y, Yang C, Ouyang P, Yin G, Huang Z et al. The preparation of bsa-plla microparticles in a batch supercritical anti-solvent process. *Carbohydr Polym* 2009;77:244–9.

- Kanthamneni N, Sharma S, Meenach SA, Billet B, Zhao J-C et al. Enhanced stability of horseradish peroxidase encapsulated in acetalated dextran microparticles stored outside cold chain conditions. *Int J Pharm* 2012;431:101–10.
- Karataş A, Sonakin O, Kiliçarslan M, Baykara T. Poly (epsilon-caprolactone) microparticles containing levobunolol hcl prepared by a multiple emulsion (w/o/w) solvent evaporation technique: effects of some formulation parameters on microparticle characteristics. *J Microencapsul* 2009;26:63–74.
- Karnchanajindanun J, Srisa-ard M, Baimark Y. Genipin-cross-linked chitosan microspheres prepared by a water-in-oil emulsion solvent diffusion method for protein delivery. *Carbohydr Polym* 2011;85:674–80.
- Katara R, Majumdar DK. Eudragit rl 100-based nanoparticulate system of aceclofenac for ocular delivery. *Colloids Surf B Biointerfaces* 2013;103:455–62.
- Katara YK, Muthukumaran T, Panda AK. Influence of particle size, antigen load, dose and additional adjuvant on the immune response from antigen loaded pla microparticles. *Int J Pharm* 2005;301:149–60.
- Kauffman KJ, Kanthamneni N, Meenach SA, Pierson BC, Bachelder EM, Ainslie KM. Optimization of rapamycin-loaded acetalated dextran microparticles for immunosuppression. *Int J Pharm* 2012;422:356–63.
- Keegan GM, Smart JD, Ingram MJ, Barnes L-M, Burnett GR, Rees GD. Chitosan microparticles for the controlled delivery of fluoride. *J Dent* 2012;40:229–40.
- Khaled KA, Sarhan HA, Ibrahim MA, Ali AH, Naguib YW. Prednisolone-loaded plga microspheres. *in vitro* characterization and *in vivo* application in adjuvant-induced arthritis in mice. *AAPS Pharm Sci Tech* 2010;11:859–69.
- Khalil NM, do Nascimento TCF, Casa DM, Dalmolin LF, de Mattos AC et al. Pharmacokinetics of curcumin-loaded plga and plga-peg blend nanoparticles after oral administration in rats. *Colloids Surf B Biointerfaces* 2013;101:353–60.
- Khalil SKH, El-Feky GS, El-Banna ST, Khalil WA. Preparation and evaluation of warfarin-β-cyclodextrin loaded chitosan nanoparticles for transdermal delivery. *Carbohydr Polym* 2012;90:1244–53.
- Khan MS, Vishakante GD, Bathool A. Development and characterization of brimonidine tartrate loaded eudragit nanosuspensions for ocular drug delivery. *J Colloid Sci Biotechnol* 2012;1:122–8.
- Khayata N, Abdelwahed W, Chehna MF, Charcosset C, Fessi H. Preparation of vitamin e loaded nanocapsules by the nanoprecipitation method: from laboratory scale to large scale using a membrane contactor. *Int J Pharm* 2012;423:419–27.
- Khoe S, Yaghoobian M. An investigation into the role of surfactants in controlling particle size of polymeric nanocapsules containing penicillin-g in double emulsion. *Eur J Med Chem* 2009;44:2392–9.
- Khoe S, Sattari A, Atyabi F. Physico-chemical properties investigation of cisplatin loaded polybutyladipate (pba) nanoparticles prepared by w/o/w. *Mater Sci Eng C* 2012;32:1078–86.
- Konecsni K, Low NH, Nickerson MT. Chitosan-tripolyphosphate submicron particles as the carrier of entrapped rutin. *Food Chem* 2012;134:1775–9.
- Koten JW, Van Luyn MJA, Cadée JA, Brouwer L, Hennink WE et al. Il-2 loaded dextran microspheres with attractive histocompatibility properties for local il-2 cancer therapy. *Cytokine* 2003;24:57–66.
- Krishnakumar N, Sulfikkarali N, Rajendra Prasad N, Karthikeyan S. Enhanced anticancer activity of naringenin-loaded nanoparticles in human cervical (hela) cancer cells. *Biomed Prev Nutr* 2011;1:223–31.
- Kumar A, Gupta GK, Khedgikar V, Gautam J, Kushwaha P et al. *In vivo* efficacy studies of layer-by-layer nano-matrix bearing kaempferol for the conditions of osteoporosis: a study in ovariectomized rat model. *Eur J Pharm Biopharm* 2012;82:508–17.
- Kumari A, Yadav SK, Pakade YB, Kumar V, Singh B et al. Nanoencapsulation and characterization of albizia chinensis isolated antioxidant quercitrin on pla nanoparticles. *Colloids Surf B Biointerfaces* 2011;82:224–32.
- Kwon H-Y, Lee J-Y, Choi S-W, Jang Y, Kim J-H. Preparation of plga nanoparticles containing estrogen by emulsification-diffusion method. *Colloids Surf Physicochem Eng Asp* 2001;182:123–30.
- Labruère R, Sicard R, Cormier R, Turos E, West L. Poly(vinyl benzoate) nanoparticles for molecular delivery: studies on their preparation and *in vitro* properties. *J Control Release* 2010;148:234–40.
- Lamalle-Bernard D, Munier S, Compagnon C, Charles M-H, Kalyanaraman VS et al. Coadsorption of hiv-1 p24 and gp120 proteins to surfactant-free anionic pla nanoparticles preserves antigenicity and immunogenicity. *J Control Release* 2006;115:57–67.

- Le Ray A-M, Chiffolleau S, Iooss P, Grimandi G, Gouyette A et al. Vancomycin encapsulation in biodegradable poly( $\epsilon$ -caprolactone) microparticles for bone implantation. influence of the formulation process on size, drug loading, in vitro release and cytocompatibility. *Biomaterials* 2003;24:443–9.
- Lee SJ, Hong G-Y, Jeong Y-I, Kang M-S, Oh J-S et al. Paclitaxel-incorporated nanoparticles of hydrophobized polysaccharide and their antitumor activity. *Int J Pharm* 2012;433:121–8.
- Lemos-Senna E, Wouessidjewe D, Duchêne D, Lesieur S. Amphiphilic cyclodextrin nanospheres: particle solubilization and reconstitution by the action of a non-ionic detergent. *Colloids Surf B Biointerfaces* 1998;10:291–301.
- Leo E, Forni F, Bernabei MT. Surface drug removal from ibuprofen-loaded pla microspheres. *Int J Pharm* 2000;196:1–9.
- Li B, Wang Q, Wang X, Wang C, Jiang X. Preparation, drug release and cellular uptake of doxorubicin-loaded dextran-b-poly( $\epsilon$ -caprolactone) nanoparticles. *Carbohydr Polym* 2013;93:430–7.
- Li P, Wang Y, Peng Z, She F, Kong L. Development of chitosan nanoparticles as drug delivery systems for 5-fluorouracil and leucovorin blends. *Carbohydr Polym* 2011;85:698–704.
- Li X, Chang S, Du G, Li Y, Gong J et al. Encapsulation of azithromycin into polymeric microspheres by reduced pressure-solvent evaporation method. *Int J Pharm* 2012;433:79–88.
- Liang D, Fu X, Liao M, Yuan W, Su J. Development of dextran microparticles loaded with il-1ra of high-encapsulation efficiency and high-bioactivity by a novel method without exposing il-1ra to water–oil interfaces. *Powder Technol* 2013;235:299–302.
- Limayem Blouza I, Charcosset C, Sfar S, Fessi H. Preparation and characterization of spironolactone-loaded nanocapsules for paediatric use. *Int J Pharm* 2006;325:124–31.
- Lince F, Marchisio DL, Barresi AA. Strategies to control the particle size distribution of poly- $\epsilon$ -caprolactone nanoparticles for pharmaceutical applications. *J Colloid Interface Sci* 2008;322:505–15.
- Ma J, Feng P, Ye C, Wang Y, Fan Y. An improved interfacial coacervation technique to fabricate biodegradable nanocapsules of an aqueous peptide solution from polylactide and its block copolymers with poly(ethylene glycol). *Colloid Polym Sci* 2001;279:387–92.
- Mahapatro A, Singh DK. Biodegradable nanoparticles are excellent vehicle for site directed in-vivo delivery of drugs and vaccines. *J Nanobiotechnol* 2011;9:55.
- Manchanda R, Fernandez-Fernandez A, Nagesetti A, McGoron AJ. Preparation and characterization of a polymeric (plga) nanoparticulate drug delivery system with simultaneous incorporation of chemotherapeutic and thermo-optical agents. *Colloids Surf B Biointerfaces* 2010;75:260–7.
- Mao S, Sun W, Kissel T. Chitosan-based formulations for delivery of dna and sirna. *Adv Drug Deliv Rev* 2010;62:12–27.
- Martin TM, Bandi N, Shulz R, Roberts CB, Kompella UB. Preparation of budesonide and budesonide-pla microparticles using supercritical fluid precipitation technology. *AAPS Pharm Sci Tech* 2002;3:E18.
- Martín-Banderas L, Alvarez-Fuentes J, Durán-Lobato M, Prados J, Melguizo C, Fernández-Arévalo M et al. Cannabinoid derivate-loaded plga nanocarriers for oral administration: formulation, characterization, and cytotoxicity studies. *Int J Nanomed* 2012;7:5793-806.
- Masson V, Maurin F, Fessi H, Devissaguet JP. Influence of sterilization processes on poly( $\epsilon$ -caprolactone) nanospheres. *Biomaterials* 1997;18:327–35.
- Maya S, Kumar LG, Sarmiento B, Sanoj Rejinold N, Menon D et al. Cetuximab conjugated o-carboxymethyl chitosan nanoparticles for targeting egfr overexpressing cancer cells. *Carbohydr Polym* 2013;93:661–9.
- Mazzaferro S, Bouchemal K, Maksimenko A, Skanji R, Opolon P, Ponchel G. Reduced intestinal toxicity of docetaxel loaded into mucoadhesive nanoparticles, in mouse xenograft model. *J Colloid Sci Biotechnol* 2012;1:210–7.
- Mazzarino L, Travelet C, Ortega-Murillo S, Otsuka I, Pignot-Paintrand I et al. Elaboration of chitosan-coated nanoparticles loaded with curcumin for mucoadhesive applications. *J Colloid Interface Sci* 2012;370:58–66.
- Mehvar R. Dextrans for targeted and sustained delivery of therapeutic and imaging agents. *J Control Release* 2000;69:1–25.

- Memişoğlu E, Bochot A, Şen M, Duchêne D, Hıncal AA. Non-surfactant nanospheres of progesterone inclusion complexes with amphiphilic  $\beta$ -cyclodextrins. *Int J Pharm* 2003;251:143–53.
- Menei P, Montero-Menei C, Venier M-C, Benoit J-P. Drug delivery into the brain using poly(lactide-co-glycolide) microspheres. *Expert Opin Drug Deliv* 2005;2:363–76.
- Miladi K, Sfar S, Fessi H, Elaissari A. Drug carriers in osteoporosis: preparation, drug encapsulation and applications. *Int J Pharm* 2013;445:181–95.
- Minost A, Delaveau J, Bolzinger M-A, Fessi H, Elaissari A. Nanoparticles via nanoprecipitation process. *Recent Pat Drug Deliv Formul* 2012;6:250–8.
- Miyazaki Y, Onuki Y, Yakou S, Takayama K. Effect of temperature-increase rate on drug release characteristics of dextran microspheres prepared by emulsion solvent evaporation process. *Int J Pharm* 2006;324:144–51.
- Mo L, Hou L, Guo D, Xiao X, Mao P, Yang X. Preparation and characterization of teniposide plga nanoparticles and their uptake in human glioblastoma u87mg cells. *Int J Pharm* 2012;436:815–24.
- Mohajel N, Najafabadi AR, Azadmanesh K, Vatanara A, Moazeni E et al. Optimization of a spray drying process to prepare dry powder microparticles containing plasmid nanocomplex. *Int J Pharm* 2012;423:577–85.
- Mora-Huertas CE, Fessi H, Elaissari A. Polymer-based nanocapsules for drug delivery. *Int J Pharm* 2010;385:113–42.
- Mora-Huertas CE, Garrigues O, Fessi H, Elaissari A. Nanocapsules prepared via nanoprecipitation and emulsification-diffusion methods: comparative study. *Eur J Pharm Biopharm* 2012;80:235–9.
- Morales-Cruz M, Flores-Fernández GM, Morales-Cruz M, Orellano EA, Rodríguez-Martínez JA et al. Two-step nanoprecipitation for the production of protein-loaded plga nanospheres. *Results Pharma Sci* 2012;2:79–85.
- Mu L, Feng S. Fabrication, characterization and in vitro release of paclitaxel (taxol®) loaded poly (lactic-co-glycolic acid) microspheres prepared by spray drying technique with lipid/cholesterol emulsifiers. *J Control Release* 2001;76:239–54.
- Muttill P, Kaur J, Kumar K, Yadav AB, Sharma R, Misra A. Inhalable microparticles containing large payload of anti-tuberculosis drugs. *Eur J Pharm Sci* 2007;32:140–50.
- Nahar M, Mishra D, Dubey V, Jain NK. Development, characterization, and toxicity evaluation of amphotericin b-loaded gelatin nanoparticles. *Nanomed Nanotechnol Biol Med* 2008;4:252–61.
- Nehilla B, Bergkvist M, Popat K, Desai T. Purified and surfactant-free coenzyme q10-loaded biodegradable nanoparticles. *Int J Pharm* 2008;348:107–14.
- O'Donnell PB, McGinity JW. Preparation of microspheres by the solvent evaporation technique. *Adv Drug Deliv Rev* 1997;28:25–42.
- Osman R, Kan PL, Awad G, Mortada N, El-Shamy A-E, Alpar O. Enhanced properties of discrete pulmonary deoxyribonuclease i (dnasei) loaded plga nanoparticles during encapsulation and activity determination. *Int J Pharm* 2011;408:257–65.
- Palazzo F, Giovagnoli S, Schoubben A, Blasi P, Rossi C, Ricci M. Development of a spray-drying method for the formulation of respirable microparticles containing ofloxacin-palladium complex. *Int J Pharm* 2013;440:273–82.
- Pariot N, Edwards-Lévy F, Andry M-C, Lévy M-C. Cross-linked  $\beta$ -cyclodextrin microcapsules. ii. retarding effect on drug release through semi-permeable membranes. *Int J Pharm* 2002;232:175–81.
- Park JH, Saravanakumar G, Kim K, Kwon IC. Targeted delivery of low molecular drugs using chitosan and its derivatives. *Adv Drug Deliv Rev* 2010;62:28–41.
- Patil SB, Sawant KK. Chitosan microspheres as a delivery system for nasal insufflation. *Colloids Surf B Biointerfaces* 2011;84:384–9.
- Péan JM, Venier-Julienne MC, Boury F, Menei P, Denizot B, Benoit JP. Ngf release from poly(d,l-lactide-co-glycolide) microspheres. effect of some formulation parameters on encapsulated ngf stability. *J Control Release* 1998;56:175–87.
- Pignatello R, Bucolo C, Ferrara P, Maltese A, Puleo A, Puglisi G. Eudragit rs100® nanosuspensions for the ophthalmic controlled delivery of ibuprofen. *Eur J Pharm Sci* 2002;16:53–61.
- Pillai O, Panchagnula R. Polymers in drug delivery. *Curr Opin Chem Biol* 2001;5:447–51.

- Pinto Reis C, Neufeld RJ, Ribeiro AJ, Veiga F. Nanoencapsulation i. methods for preparation of drug-loaded polymeric nanoparticles. *Nanomed Nanotechnol Biol Med* 2006;2:8–21.
- Poletto FS, Fiel LA, Donida B, Ré MI, Guterres SS, Pohlmann AR. Controlling the size of poly(hydroxybutyrate-co-hydroxyvalerate) nanoparticles prepared by emulsification–diffusion technique using ethanol as surface agent. *Colloids Surf Physicochem Eng Asp* 2008;324:105–12.
- Powell TJ, Palath N, DeRome ME, Tang J, Jacobs A, Boyd JG. Synthetic nanoparticle vaccines produced by layer-by-layer assembly of artificial biofilms induce potent protective t-cell and antibody responses in vivo. *Vaccine* 2011;29:558–69.
- Prata AS, Garcia L, Tonon RV, Hubinger MD. Wall material selection for encapsulation by spray drying. *J Colloid Sci Biotechnol* 2013;2:86–92.
- Prior S, Gamazo C, Irache J, Merkle H, Gander B. Gentamicin encapsulation in pla/plga microspheres in view of treating brucella infections. *Int J Pharm* 2000;196:115–25.
- Qi W, Yan X, Fei J, Wang A, Cui Y, Li J. Triggered release of insulin from glucose-sensitive enzyme multilayer shells. *Biomaterials* 2009;30:2799–806.
- Quintanar-Guerrero D, Fessi H, Allémann E, Doelker E. Influence of stabilizing agents and preparative variables on the formation of poly(d,l-lactic acid) nanoparticles by an emulsification-diffusion technique. *Int J Pharm* 1996;143:133–41.
- Radtchenko IL, Sukhorukov GB, Möhwald H. Incorporation of macromolecules into polyelectrolyte micro- and nanocapsules via surface controlled precipitation on colloidal particles. *Colloids Surf Physicochem Eng Asp* 2002;202:127–33.
- Raffin RP, Colomé LM, Schapoval EES, Pohlmann AR, Guterres SS. Increasing sodium pantoprazole photostability by microencapsulation: effect of the polymer and the preparation technique. *Eur J Pharm Biopharm* 2008;69:1014–8.
- Rao JP, Geckeler KE. Polymer nanoparticles: preparation techniques and size-control parameters. *Prog Polym Sci* 2011;36:887–913.
- Rattes ALR, Oliveira WP. Spray drying conditions and encapsulating composition effects on formation and properties of sodium diclofenac microparticles. *Powder Technol* 2007;171:7–14.
- Raval JP, Naik DR, Amin KA, Patel PS. Controlled-release and antibacterial studies of doxycycline-loaded poly( $\epsilon$ -caprolactone) microspheres. *J Saudi Chem Soc*, 2011, epub ahead of print, <http://dx.doi.org/10.1016/j.jscs.2011.11.004>
- Rawat A, Burgess DJ. Effect of ethanol as a processing co-solvent on the plga microsphere characteristics. *Int J Pharm* 2010;394:99–105.
- Rees DA, Welsh EJ. Secondary and tertiary structure of polysaccharides in solutions and gels. *Angew Chem Int Ed Engl* 1977;16:214–24.
- Rosset V, Ahmed N, Zaanoun I, Stella B, Fessi H, Elaissari A. Elaboration of argan oil nanocapsules containing naproxen for cosmetic and transdermal local application. *J Colloid Sci Biotechnol* 2012;1:218–24.
- Ruan G, Feng S-S. Preparation and characterization of poly(lactic acid)–poly(ethylene glycol)–poly(lactic acid) (pla–peg–pla) microspheres for controlled release of paclitaxel. *Biomaterials* 2003;24:5037–44.
- Sacchetin PSC, Morales AR, Moraes ÂM, Rosa P de TV e. Formation of pla particles incorporating 17 $\alpha$ -methyltestosterone by supercritical fluid technology. *J Supercrit Fluids* 2013;77:52–62.
- Sajadi Tabassi SA, Tafaghodi M, Jaafari MR. Induction of high antitoxin titers against tetanus toxoid in rabbits by intranasal immunization with dextran microspheres. *Int J Pharm* 2008;360:12–7.
- Sane A, Limtrakul J. Formation of retinyl palmitate-loaded poly(l-lactide) nanoparticles using rapid expansion of supercritical solutions into liquid solvents (resolv). *J Supercrit Fluids* 2009;51:230–7.
- Sanli D, Bozbag SE, Erkey C. Synthesis of nanostructured materials using supercritical co<sub>2</sub>: part i. physical transformations. *J Mater Sci* 2012;47:2995–3025.
- Santos DT, Albarelli JQ, Beppu MM, Meireles MAA. Stabilization of anthocyanin extract from jaboticaba skins by encapsulation using supercritical co<sub>2</sub> as solvent. *Food Res Int* 2013;50:617–24.
- Sastre RL, Olmo R, Teijón C, Muñiz E, Teijón JM, Blanco MD. 5-fluorouracil plasma levels and biodegradation of subcutaneously injected drug-loaded microspheres prepared by spray-drying poly(d,l-lactide) and poly(d,l-lactide-co-glycolide) polymers. *Int J Pharm* 2007;338:180–90.

- Seju U, Kumar A, Sawant KK. Development and evaluation of olanzapine-loaded plga nanoparticles for nose-to-brain delivery: in vitro and in vivo studies. *Acta Biomater* 2011;7:4169–76.
- Seo D-H, Jeong Y-I, Kim D-G, Jang M-J, Jang M-K, Nah J-W. Methotrexate-incorporated polymeric nanoparticles of methoxy poly(ethylene glycol)-grafted chitosan. *Colloids Surf B Biointerfaces* 2009;69:157–63.
- Seremeta KP, Chiappetta DA, Sosnik A. Poly( $\epsilon$ -caprolactone), eudragit® rs 100 and poly( $\epsilon$ -caprolactone)/eudragit® rs 100 blend submicron particles for the sustained release of the antiretroviral efavirenz. *Colloids Surf B Biointerfaces* 2013;102:441–9.
- Shao Y, Zhu B, Li J, Liu X, Tan X, Yang X. Novel chitosan microsphere-templated microcapsules suitable for spontaneous loading of heparin. *Mater Sci Eng C* 2009;29:936–41.
- Silva AL, Rosalia RA, Sazak A, Carstens MG, Osendorp F et al. Optimization of encapsulation of a synthetic long peptide in plga nanoparticles: low-burst release is crucial for efficient cd8(+) t cell activation. *Eur J Pharm Biopharm* 2013;83:338–45.
- Simşek S, Eroğlu H, Kurum B, Ulubayram K. Brain targeting of atorvastatin loaded amphiphilic plga-b-peg nanoparticles. *J Microencapsul* 2013;30:10–20.
- Singh M, Kazzaz J, Ugozzoli M, Chesko J, O'Hagan DT. Charged polylactide co-glycolide microparticles as antigen delivery systems. *Expert Opin Biol Ther* 2004;4:483–91.
- Sinha VR, Bansal K, Kaushik R, Kumria R, Trehan A. Poly-epsilon-caprolactone microspheres and nanospheres: an overview. *Int J Pharm* 2004;278:1–23.
- Siqueira-Moura MP, Primo FL, Espreafico EM, Tedesco AC. Development, characterization, and photocytotoxicity assessment on human melanoma of chloroaluminum phthalocyanine nanocapsules. *Mater Sci Eng C* 2013;33:1744–52.
- Soares ASP. A special issue on applications of microencapsulation. *J Colloid Sci Biotechnol* 2013;2:77.
- Sollohub K, Cal K. Spray drying technique: ii. current applications in pharmaceutical technology. *J Pharm Sci* 2010;99:587–97.
- Song KC, Lee HS, Choung IY, Cho KI, Ahn Y, Choi EJ. The effect of type of organic phase solvents on the particle size of poly(d,l-lactide-co-glycolide) nanoparticles. *Colloids Surf Physicochem Eng Asp* 2006;276:162–7.
- Song X, Zhao Y, Wu W, Bi Y, Cai Z et al. Plga nanoparticles simultaneously loaded with vincristine sulfate and verapamil hydrochloride: systematic study of particle size and drug entrapment efficiency. *Int J Pharm* 2008;350:320–9.
- Sou T, Meeusen EN, de Veer M, Morton DAV, Kaminskas LM, McIntosh MP. New developments in dry powder pulmonary vaccine delivery. *Trends Biotechnol* 2011;29:191–8.
- Souguir H, Salaün F, Douillet P, Vroman I, Chatterjee S. Nanoencapsulation of curcumin in polyurethane and polyurea shells by an emulsion diffusion method. *Chem Eng J* 2013;221:133–45.
- Stulzer HK, Tagliari MP, Parize AL, Silva MAS, Laranjeira MCM. Evaluation of cross-linked chitosan microparticles containing acyclovir obtained by spray-drying. *Mater Sci Eng C* 2009;29:387–92.
- Su Z, Sun F, Shi Y, Jiang C, Meng Q et al. Effects of formulation parameters on encapsulation efficiency and release behavior of risperidone poly(d,l-lactide-co-glycolide) microsphere. *Chem Pharm Bull (Tokyo)* 2009;57:1251–6.
- Sukhorukov GB, Donath E, Lichtenfeld H, Knippel E, Knippel M et al. Layer-by-layer self assembly of polyelectrolytes on colloidal particles. *Colloids Surf Physicochem Eng Asp* 1998;137:253–66.
- Suksiriworapong J, Sripha K, Kreuter J, Junyaprasert VB. Functionalized (poly( $\epsilon$ -caprolactone))<sub>2</sub>-poly(ethyleneglycol) nanoparticles with grafting nicotinic acid as drug carriers. *Int J Pharm* 2012;423:562–70.
- Surassmo S, Min S-G, Bejrapha P, Choi M-J. Effects of surfactants on the physical properties of capicum oleoresin-loaded nanocapsules formulated through the emulsion-diffusion method. *Food Res Int* 2010;43:8–17.
- Tawfeek HM. Evaluation of peg and mpeg-co-(pga-co-pdl) microparticles loaded with sodium diclofenac. *Saudi Pharm J* 2013;21:387–97.
- Tewa-Tagne P, Briançon S, Fessi H. Spray-dried microparticles containing polymeric nanocapsules: formulation aspects, liquid phase interactions and particles characteristics. *Int J Pharm* 2006;325:63–74.

- Thomas C, Gupta V, Ahsan F. Influence of surface charge of plga particles of recombinant hepatitis b surface antigen in enhancing systemic and mucosal immune responses. *Int J Pharm* 2009;379:41–50.
- Trapani A, Laquintana V, Denora N, Lopedota A, Cutrignelli A et al. Eudragit rs 100 microparticles containing 2-hydroxypropyl- $\beta$ -cyclodextrin and glutathione: physicochemical characterization, drug release and transport studies. *Eur J Pharm Sci* 2007;30:64–74.
- Tse MT, Blatchford C, Oya Alpar H. Evaluation of different buffers on plasmid dna encapsulation into plga microparticles. *Int J Pharm* 2009;370:33–40.
- Valot P, Baba M, Nedelec J-M, Sintes-Zydowicz N. Effects of process parameters on the properties of biocompatible ibuprofen-loaded microcapsules. *Int J Pharm* 2009;369:53–63.
- Van de Ven H, Vermeersch M, Matheussen A, Vandervoort J, Weyenberg W et al. Plga nanoparticles loaded with the antileishmanial saponin  $\beta$ -aescin: factor influence study and in vitro efficacy evaluation. *Int J Pharm* 2011;420:122–32.
- Van de Ven H, Paulussen C, Feijens PB, Matheussen A, Rombaut P et al. Plga nanoparticles and nanosuspensions with amphotericin b: potent in vitro and in vivo alternatives to fungizone and ambisome. *J Control Release* 2012;161:795–803.
- Van der Graaf S, Schroën CGPH, Boom RM. Preparation of double emulsions by membrane emulsification—a review. *J Membr Sci* 2005;251:7–15.
- Vanderhoff JW, El-Aasser MS, Ugelstad J. Polymer emulsification process. U.S. Patent 4,177,177, December 1979.
- Vandervoort J, Ludwig A. Preparation and evaluation of drug-loaded gelatin nanoparticles for topical ophthalmic use. *Eur J Pharm Biopharm* 2004;57:251–61.
- Vauthier C, Bouchemal K. Methods for the preparation and manufacture of polymeric nanoparticles. *Pharm Res* 2009;26:1025–58.
- Vergaro V, Scarlino F, Bellomo C, Rinaldi R, Vergara D et al. Drug-loaded polyelectrolyte microcapsules for sustained targeting of cancer cells. *Adv Drug Deliv Rev* 2011;63:847–64.
- Vila A, Gill H, McCallion O, Alonso MJ. Transport of pla-peg particles across the nasal mucosa: effect of particle size and peg coating density. *J Control Release* 2004;98:231–44.
- Vila A, Sánchez A, Évora C, Soriano I, McCallion O, Alonso MJ. Pla-peg particles as nasal protein carriers: the influence of the particle size. *Int J Pharm* 2005;292:43–52.
- Vladislavljević GT, Williams RA. Recent developments in manufacturing particulate products from double-emulsion templates using membrane and microfluidic devices. In: Aserin A (ed.): *Multiple emulsions: technology and applications* (pp 121-64). New York: Wiley, 2008.
- Wang F-J, Wang C-H. Sustained release of etanidazole from spray dried microspheres prepared by non-halogenated solvents. *J Control Release* 2002;81:263–80.
- Wang G, Yu B, Wu Y, Huang B, Yuan Y, Liu CS. Controlled preparation and antitumor efficacy of vitamin e tpgs-functionalized plga nanoparticles for delivery of paclitaxel. *Int J Pharm* 2013;446:24–33.
- Wang S, Guo S, Cheng L. Disodium norcantharidate loaded poly( $\epsilon$ -caprolactone) microspheres: i. preparation and evaluation. *Int J Pharm* 2008;350:130–7.
- Xie H, Smith JW. Fabrication of plga nanoparticles with a fluidic nanoprecipitation system. *J Nanobiotechnol* 2010;8:18.
- Xin H, Chen L, Gu J, Ren X, Wei Z, et al. Enhanced anti-glioblastoma efficacy by ptx-loaded pegylated poly( $\epsilon$ -caprolactone) nanoparticles: in vitro and in vivo evaluation. *Int J Pharm* 2010;402:238–47.
- Yadav KS, Sawant KK. Formulation optimization of etoposide loaded plga nanoparticles by double factorial design and their evaluation. *Curr Drug Deliv* 2010;7:51–64.
- Yan S, Zhu J, Wang Z, Yin J, Zheng Y, Chen X. Layer-by-layer assembly of poly(l-glutamic acid)/chitosan microcapsules for high loading and sustained release of 5-fluorouracil. *Eur J Pharm Biopharm* 2011;78:336–45.
- Yang J, Park S-B, Yoon H-G, Huh Y-M, Haam S. Preparation of poly  $\epsilon$ -caprolactone nanoparticles containing magnetite for magnetic drug carrier. *Int J Pharm* 2006;324:185–90.
- Yang Z, Birkenhauer P, Julmy F, Chickering D, Raniere JP et al. Sustained release of heparin from polymeric particles for inhibition of human vascular smooth muscle cell proliferation. *J Control Release* 1999;60:269–77.

- Yildiz A, John E, Özsoy Y, Araman A, Birchall JC et al. Inhaled extended-release microparticles of heparin elicit improved pulmonary pharmacodynamics against antigen-mediated airway hyper-reactivity and inflammation. *J Control Release* 2012;162:456–63.
- Yoncheva K, Gómez S, Campanero MA, Gamazo C, Irache JM. Bioadhesive properties of pegylated nanoparticles. *Expert Opin Drug Deliv* 2005;2:205–18.
- Yoo M-K, Kang S-K, Choi J-H, Park I-K, Na H-S et al. Targeted delivery of chitosan nanoparticles to peyer's patch using m cell-homing peptide selected by phage display technique. *Biomaterials* 2010;31:7738–47.
- Yordanov G. Influence of the preparation method on the physicochemical properties of econazole-loaded poly(butyl cyanoacrylate) colloidal nanoparticles. *Colloids Surf Physicochem Eng Asp* 2012;413:260–5.
- Youm I, Murowchick JB, Youan B-BC. Entrapment and release kinetics of furosemide from pegylated nanocarriers. *Colloids Surf B Biointerfaces* 2012;94:133–42.
- Young S, Wong M, Tabata Y, Mikos AG. Gelatin as a delivery vehicle for the controlled release of bioactive molecules. *J Control Release* 2005;109:256–74.
- Zakeri-Milani P, Loveymi BD, Jelvehgari M, Valizadeh H. The characteristics and improved intestinal permeability of vancomycin plga-nanoparticles as colloidal drug delivery system. *Colloids Surf B Biointerfaces* 2013;103:174–81.
- Zambaux MF, Bonneaux F, Gref R, Maincent P, Dellacherie E et al. Influence of experimental parameters on the characteristics of poly(lactic acid) nanoparticles prepared by a double emulsion method. *J Control Release* 1998;50:31–40.
- Zandanel C, Vauthier C. Poly (isobutylcyanoacrylate) nanoparticles decorated with chitosan: effect of conformation of chitosan chains at the surface on complement activation properties. *J Colloid Sci Biotechnol* 2012;1:68–81.
- Zhang C, Li G, Wang Y, Cui F, Zhang J, Huang Q. Preparation and characterization of 5-fluorouracil-loaded plla-peg/peg nanoparticles by a novel supercritical co2 technique. *Int J Pharm* 2012;436:272–81.
- Zhang F, Wu Q, Chen Z-C, Zhang M, Lin X-F. Hepatic-targeting microcapsules construction by self-assembly of bioactive galactose-branched polyelectrolyte for controlled drug release system. *J Colloid Interface Sci* 2008a;317:477–84.
- Zhang F, Wu Q, Liu L-J, Chen Z-C, Lin X-F. Thermal treatment of galactose-branched polyelectrolyte microcapsules to improve drug delivery with reserved targetability. *Int J Pharm* 2008b;357:22–31.
- Zhang H, Cui W, Bei J, Wang S. Preparation of poly(lactide-co-glycolide-co-caprolactone) nanoparticles and their degradation behaviour in aqueous solution. *Polym Degrad Stab* 2006;91:1929–36.
- Zhao H, Gagnon J, Hafeli UO. Process and formulation variables in the preparation of injectable and biodegradable magnetic microspheres. *Biomagn Res Technol* 2007;5:2.
- Zheng X, Kan B, Gou M, Fu S, Zhang J et al. Preparation of mpeg-pla nanoparticle for honokiol delivery in vitro. *Int J Pharm* 2010;386:262–7.
- Zhou YZ, Alany RG, Chuang V, Wen J. Optimization of plga nanoparticles formulation containing l-dopa by applying the central composite design. *Drug Dev Ind Pharm* 2013;39:321–30.
-